

# Synthesis of (Ti/Si) mixed oxides for the removal of Cr(VI) in simulated effluents

## Síntesis de óxidos mixtos (Ti/Si) CO para la remoción de Cr(VI) en efluentes simulados

Gloria María Doria-Herrera <sup>1\*</sup>, Nelson A. Ledesma <sup>2</sup>, Juan A. Gutiérrez-Vélez <sup>3</sup>, Hoover A. Valencia <sup>4</sup>, Héctor Fabio Cortés-Hernández <sup>5</sup>

<sup>1</sup>Grupo de Investigación en Físicoquímica Aplicada y Modelado Molecular GIFAMol, Universidad EAFIT. Carrera 49 # 7 Sur 50. C. P. 11001. Medellín, Colombia.

<sup>2</sup>Facultad de Ingeniería, Universidad EAFIT. Carrera 49 # 7 Sur 50. C. P. 11001. Medellín, Colombia.

<sup>3</sup>Laboratorio de Estupecientes, Universidad de Antioquia, Calle 67 # 53 – 108. C. P. 050010. Medellín, Colombia.

<sup>4</sup>Escuela de Química, Grupo de Investigación en Físicoquímica Aplicada y Modelado Molecular GIFAMol, Universidad Tecnológica de Pereira. Calle 11 # 27 15. C. P. 660003. Pereira, Colombia.

<sup>5</sup>Facultad de Ciencias, Departamento de Química, Grupo de Investigación en Físicoquímica Aplicada y Modelado Molecular GIFAMol, Universidad del Tolima. Calle 42 # 1B-1. C. P. 730006299. Ibagué, Colombia.



### CITE THIS ARTICLE AS:

G. M. Doria-Herrera, N. A. Ledesma, J. A. Gutiérrez-Vélez, H. A. Valencia and H. F. Cortés-Hernández. "Synthesis of (Ti/Si) mixed oxides for the removal of Cr(VI) in simulated effluents", *Revista Facultad de Ingeniería Universidad de Antioquia*, no. 118, pp. e50674, Jan-Mar 2026. [Online]. Available: <https://www.doi.org/10.17533/udea.redin.20250674>

### ARTICLE INFO:

Received: October 24, 2024

Accepted: June 10, 2025

Available online: June 10, 2025

### KEYWORDS:

Waste treatment; composite material; metals; pollutants; experimental methods

Contaminación del agua; material compuesto; metales; contaminantes; métodos experimentales

**ABSTRACT:** The use of agroindustry residues as precursor materials in the absorption processes has taken a significant importance due to their great absorptive porous characteristics; however, the most critical drawback of the heavy metals is the difficulty of eliminating them, particularly, the Cr(VI), which is widely used in tannery but, at the same time, is considered a powerful cancerogenic and mutagenic agent. For this reason, it is crucial to seek strategies to eliminate, or form complexes for future immobilization, such heavy metals. This research proposes the synthesis of a mix of silica/titanium (Si/Ti) using the rice husk as the source of silica, and titanium tetrachloride as a precursor of titanium for the removal of the Cr(VI) in simulated effluents. TGA, IR-ATR analysis, SEM, powder diffraction and fluorescence were applied to verify the efficiency of the reaction and the adsorptive capacity. Three variables were considered significant in the adsorption process: pH; amount of dosage; and concentration of Cr(VI) contaminant, which were assessed independently for silica oxide, from which a removal rate of 53.4%, pH 1, 1.5 g adsorbent/L and initial concentration of Cr(VI) 0.08 mg/L was obtained. For the mixed oxide from a removal percentage of 97.2% was obtained, with the best removal conditions at a pH of 1.5 g/L adsorbent dosage amount and Cr(VI) contaminant concentration of 0.08 mg/L.

**RESUMEN:** El uso de residuos de la agroindustria como materiales precursores en los procesos de absorción ha tomado una importancia significativa debido a que tienen grandes características de porosidad absorbente; sin embargo, el mayor inconveniente de los metales pesados es la dificultad que presentan para ser eliminados, en particular, el Cr(VI), que es ampliamente utilizado en curtiembres y considerado como un poderoso agente cancerígeno y mutagénico. Por ello, es importante la búsqueda de estrategias para su eliminación o acomplejar para la inmovilización. Esta investigación propone la síntesis de una mezcla sílice/titanio (Si/Ti) utilizando cascarilla de arroz como fuente de sílice y, como precursor del titanio, tetracloruro de titanio para la remoción del Cr(VI) en efluentes simulados. Para verificar la caracterización de la síntesis y comprobar las propiedades adsorptivas se usó TGA, análisis IR-ATR, SEM, difracción de polvo y fluorescencia. Se identificaron tres variables significativas en el proceso de adsorción: pH; cantidad de dosificación; y concentración de Cr(VI) contaminante, y se aplicaron de forma independiente para el óxido de sílice, del cual se obtuvo una tasa de remoción del 53,4%, pH 1, 1.5 g adsorbente/L y concentración inicial de Cr(VI) 0,08 mg/L.

Para el óxido mixto se obtuvo un porcentaje de remoción del 97,2%, con las mejores condiciones de remoción a un pH de 1,5 g/L de dosis de adsorbente y concentración de contaminante Cr(VI) de 0,08 mg/L.

\* Corresponding author: Gloria María Doria-Herrera

E-mail: [gmdorih@eafit.edu.co](mailto:gmdorih@eafit.edu.co)

ISSN 0120-6230

e-ISSN 2422-2844

## 1. Introduction

The search for new inexpensive and efficient materials for the treatment of effluents contaminated with heavy metals has been of great interest due to their environmental impact and the challenge that poses their difficult removal because of pH fluctuations (formation of microspecies) [1, 2]. There are conventional methodologies in place, such as the electrochemical process, membrane filtration, and ionic interchange; however, those methods imply excessive operation cost, incomplete removal, sludge formation and generation of toxic by-products [3]. For this reason, the need to propose alternative treatment strategies that apply affordable, efficient, and environmentally friendly methodologies was identified. The adsorption processes are considered an option that meets these characteristics and that, in addition, takes advantage of agroindustry residues, which are otherwise commonly problematic due to their accumulation and difficult disposal, providing added value to these processes [4]. On the other hand, the binary composites, such as mixed transition metal oxides, present a very wide range of electronic properties, which makes them functional materials in various applications. Specifically for the case of this research, the silica and titanium oxides can be applied in photocatalysis [5] and heavy metal adsorption [6].

There are two species of rice seedlings that can be considered primary: *Oryza glaberrima* and *Oryza Sativa* L. The first species is grown almost exclusively in West Africa [7]; the second, constitutes the predominant species in terms of rice cultivation worldwide. It originates from Asia and, thanks to advances in genetic engineering, there are countless varieties of this species cultivated on the planet; the Miramono and Fedearroz 2000 Colombian varieties are prevalent in the rice-growing regions of the country [8].

This research proposes the synthesis of a mix of silica/Titanium Oxide (Si/Ti), using  $SiO_2$  from rice husk and titanium chloride precursor, to evaluate its capacity as adsorbent in the removal of Cr(VI) from simulated wastewater. Subsequently, for the characterization of the synthesized composite, thermogravimetric analysis (TGA), infrared spectroscopy with attenuated reflectance (IR-ATR) analysis, scanning electron microscopy (SEM), powder diffraction, and fluorescence were applied to check the formation of the new composite. At last, for the quantification of the adsorption capacity, a simultaneous study of the effects of the several variables in the Cr(VI) adsorption process such as pH, dosage of the adsorbent was performed, and subsequently, the initial concentration of the pollutant was determined in order to establish the environmental conditions that yield the best percentages in the removal of Cr(VI) [9].

## 2. Materials and methods

### 2.1 Sample collection of rice seedlings and rice husks from agroindustry residue

The rice seedlings and husks were obtained in two different regions of Colombia, specifically from Córdoba and Norte de Santander. These seedlings were taken for botanical identification at the University of Antioquia Herbarium (HUA), where information about the species and family of the specimens was obtained.

### 2.2 Preparation of rice husk samples

The rice husks from each of the regions were separately washed with distilled water to remove impurities, then dried at 100 °C in forced air oven for a period of 48 hours until moisture removal. The husks were later stored in sealed polyethylene bags for the next testing. Then, to collect the ashes from of the rice husk, 10 g of rice husk were calcined in a heating muffle at a temperature of 800 °C. At last, the calcined material was cooled for 2 hours and used for  $SiO_2$  extraction [10].

### 2.3 Extraction of amorphous silica

For the extraction process, the rice husk ash (CCA) extracted in the above process was added to 100 mL of a 2.5 M aqueous NaOH solution at room temperature with constant stirring for 30 min, which was later heated at 120 °C for 20 minutes. The resulting slurry was filtered hot in a vacuum system. The ash residue retained on the paper was washed with hot distilled water to solubilize the sodium silicate. The filtration was later cooled and adjusted to pH 2 by adding 2.5 M  $H_2SO_4$  to precipitate the silica. The precipitated solid was dried at 120 °C in a forced air oven for 15 hours, washed with distilled water to remove the impurities and, at last, dried again at 60 °C for 48 hours [11].

### 2.4 Synthesis of the mixed composite

For the synthesis of the composite, a concentration of 0.5 M  $TiCl_4$  in 3 M HCl was prepared. The mixture was then transferred to a pre-weighed flat bottom balloon, and then  $SiO_2$  (23.95 g) was added in a mass ratio proportion of 1:1 of  $SiO_2 : TiCl_4$ . The mixture was refluxed with constant stirring at 300 rpm and 95 °C in oil bath for 2 hours.

### 2.5 Quantification of the Cr(VI) in the solution

For the quantification of Hexavalent Chromium, the colorimetric technique described in edition 22 of the standard methods for the analysis of potable and residual

**Table 1** Minimum and maximum ranges for the development of the DCC

Range	Initial Conc. (ppm)	pH	Dosage (g/L)
Minimum	0.08	1.0	0.30
Maximum	0.80	5.00	5.00

water, Method 3500-Cr B (Page 3-69 to 3-70) was used. Then, 10 minutes after preparing the reagent, absorbance was measured on the UVmini-1240 spectrophotometer at a wavelength of 540 nm.

## 2.6 Experimental design for the test

The following parameters were used in the adsorption process: Cr(VI) initial concentration; pH; and adsorbent dosage [12]. The selection criterion of low (-) and high (+) pH levels is associated to the preference of the polluting species at an acid pH [13]. To establish the adsorption process criteria, and with the help of statistical software Statgraphics 19-X64, an experimental design was developed using factorial design with three points to the center. Table 1 illustrates the minimum and maximum ranges of each of the parameters taken for the elaboration of the central composite design (DCC) for triplicate experiments.

## 2.7 Characterization techniques

The rice ash, silica and mixed oxide compounds obtained were characterized by using X-ray fluorescence (FRX) techniques, with FRX X ARL 9800XP equipment, at Cementos Argos S.A. Santa Bárbara station; X-ray diffraction (XRD) with Bruker D8 Advance and TGA equipment, NETZSCH TG 209 F1, at the Interdisciplinary Institute of Sciences of Universidad del Quindío; Fourier Transform Infrared Spectroscopy (FTIR-ATR) with PerkinElmer Spectrum Two, in the Applied Chemistry Laboratory of Universidad Nacional de Colombia, Medellín; and SEM and X-ray Dispersive Energy Spectrometry Coupled to Scanning Electron Microscopy (EDS), with JSM-7100F Field Emission Scanning Electron Microscope, In The Laboratory Of Microscopy of ITM, Medellín, Colombia.

## 3. Results and discussion

### 3.1 Identification of rice seedlings

The rice seedlings used for this research originated from the Colombian regions of Córdoba and Norte de Santander, these samples were classified by the HUA. The results indicated that both specimens belong to the species *Oryza*

*sativa* L. of the *Poaceae* family; the specimen from the Córdoba department corresponds to the variety of Creole rice known as Miramono and the specimen obtained from the rice-growing region of Norte de Santander belongs to the variety known as Fedearroz 2000. The results show that there is no significant difference in terms of species and family for both samples collected. The yield in the process of extracting silica from the CCA from Córdoba region was 81.35 %, while the variety from Norte de Santander was 78.82 %. The silica extraction showed losses of 12 and 15 % with respect to the amorphous  $SiO_2$ , which was 92.8 % in the CCA from Córdoba region and 95.8 % in the Norte de Santander variety.

### 3.2 Silica extraction from rice husk

In the extraction process, during the first 15 minutes, an almost brownish-yellowish coloration was observed, this has been described as the solubilization of the silica present in the ash by the formation of the  $Na_2SiO_3$  suspension aggregate [14]. In the next stage, as the acidification process progressed, precipitated silica began to appear. Then, in the neutralization phase, the formation of a thick, white gel was observed, which was later dried [15].

After drying the gel, a white paste was obtained, which was washed, filtered, dried, and pulverized to obtain a fine powder as shown in Figure 1. The yield of the silica extraction in the CCA from the Córdoba region was 81.35 %, while in the extraction of CCA from the Norte de Santander region was 78.82 %, this means that, out of every 100 g of ash that were chemically treated with the previously described procedure, 81.35 g and 78.82 g were recovered, respectively. This indicates silica losses of 12 % and 15 % with respect to the amorphous silica content, which is 92.8 % in the CCA from the Córdoba region and 95.8 % in the CCA from the Norte de Santander region (this information will be expanded upon later in the elemental analysis of CCA). These losses of material are due to different factors: First, the silica in the gel phase (intermediate step in the extraction process) tended to remain adhered to the glass material; second, when filtering the material, the finer particles passed through the sieve; and finally, the silica powders were too fine and when handled they remained suspended in the air or adhered to other surfaces; these factors together made it difficult to recover the extracted material.

Later, the synthesized product became a very fine powder of white color, shown in Figure 2, its mass was measured at 20.45 g and the yield of the process was calculated at 60.02 % of the theoretical basis that was 34.07 g that would be generated from the 1:1 mass ratio of  $TiCl_4$  and amorphous  $SiO_2$  [16].



**Figure 1** Products of the different steps of the amorphous silica extraction: (a) digestion of CCA in 2.5 M NaOH, (b) filtration of  $Na_2SO_3$ , (c) silica gel, (d) amorphous silica



**Figure 2** Reflux assembly for the synthesis of mixed oxides [ $TiO_2/SiO_2$ ]

The results of the white appearance and the fineness of the mixed oxides are a characteristic trait of this type of composites [17].

### 3.3 Characterization of the $TiO_2/SiO_2$ composite

#### FRX analysis

The above results of a 92 % content of silica (Si) in the ashes from the Córdoba and Norte de Santander make a significant match in comparison to previous research, with between 85 % and 96 % [18]. Table 2 shows the elemental composition of the ashes, and the silica derived from the ashes of each region; the presence of potassium, calcium, and phosphorus oxides among others; as well as minerals commonly found in rice husks [18, 19]. These experiments presented a successful extraction of the silica from the ash of the rice husk. The FRX analysis showed that amorphous  $SiO_2$  was obtained with a purity percentage of 97 %, the remaining 3 % was comprised of metal oxides derived from the husk ash; it should be noted that the concentrations of these oxides decreased significantly.

The elemental FRX analysis shows the presence of Mercury in the CCA and amorphous  $SiO_2$ . The presence of this heavy metal in the CCA and its amorphous  $SiO_2$  can be attributed to the absorption of mercury by the roots


of the rice seedlings from the surrounding medium or the flood or saturation water used in the irrigation of the crop [20, 21]. The FRX analysis applied to the mixed oxides reveals that their elemental composition is of silica, at 72.30 %, followed by titanium, at 26.60 %, and, to a lesser extent, traces of mercury and other metallic elements in percentages of 0.70 and 0.42 respectively. The explanation for the presence of oxides is attributed to the natural source of the  $SiO_2$ , which is very similar to the results presented in the previous research [14, 21]. Finally, the results of this analysis regarding synthetized composite  $TiO_2/SiO_2$  are consistent to previous research, with around 26 % using the precursor  $TiCl_4$  [22].

#### XRD analysis

XRD diffractograms of the CCA of the Córdoba and Norte de Santander regions shown in the Figure 3 appeared in a band between  $(15^\circ-30^\circ)$  with a prominent peak that reaches its maximum in the mark of  $22^\circ$ , which is consistent with previous research, where it is mentioned as a characteristic of the ashes of the rice husk and is closely related to the amorphous silica [23]. On the other hand, the silica extracted from the ashes of both regions shows the same patterns in their respective diffractograms. Figure 3 shows the amorphous  $SiO_2$  diffractograms of both regions [21, 22]. Based on the diffractograms obtained from the rice husks and the silica from both regions in Figure 3, it can be affirmed that the ash obtained presents high

**Table 2** Elemental composition of CCA and mixed oxides  $TiO_2/SiO_2$ 

Composition (%)	Source				
	CCA-Cord	CCA-Norte de S.	SiO <sub>2</sub> -Cord.	SiO <sub>2</sub> - Norte de S.	TiO <sub>2</sub> /SiO <sub>2</sub>
Si	92.80	95.80	97.10	97.90	72.30
K	3.59	1.06	0.36	0.31	–
Ca	1.07	0.75	0.16	0.18	–
Hg	0.70	0.54	1.64	1.09	0.68
P	0.65	0.52	0.13	0 –	–
Ti	–	–	–	–	26.26
Others	1.19	1.32	0.61	0.52	0.42

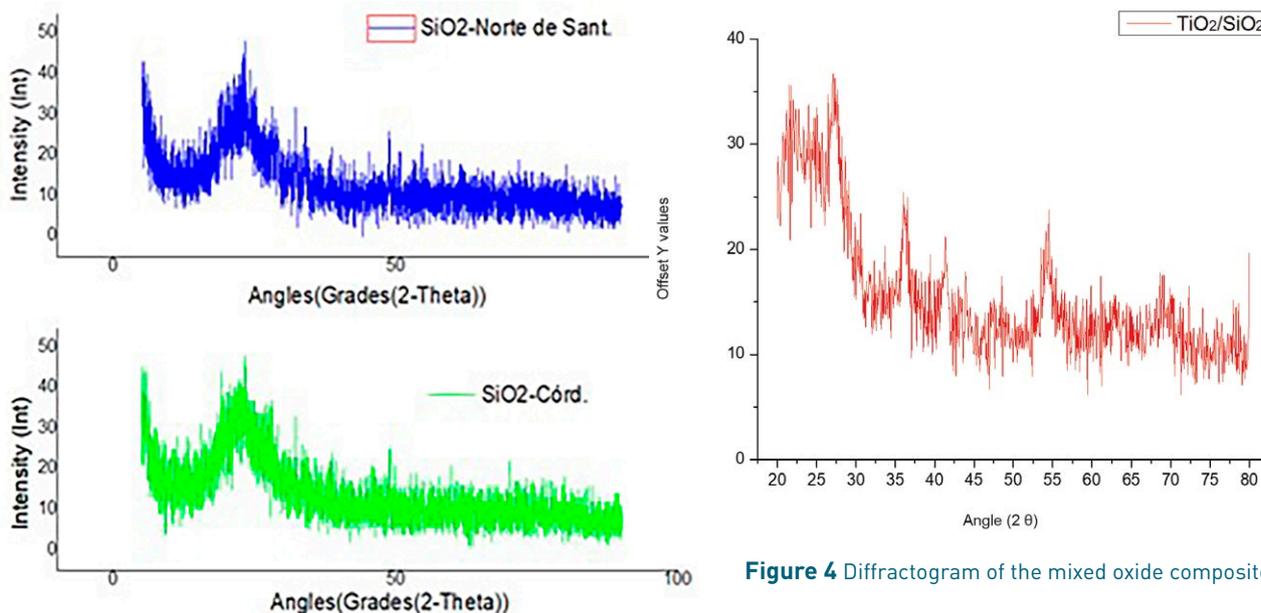**Figure 3** Diffractograms of the silica Córdoba Region and Norte de Santander Region


contents of silica. In addition, both silica samples, present in the ashes and the extracted silica, exhibit characteristics typical of the amorphous silica, and additionally, the calcination at 800 °C did not cause significant variation in the morphology of the crystalline lattice of the silica extracted [24, 25]. Furthermore, the diffractogram from the DRX analysis applied to the mixed oxides composite (Figure 4) shows a continuous band that is only interrupted at 27° by the formation of a peak in this band; this can be associated with amorphous  $SiO_2$ . Different peaks are present in the 36, 42, 54, and 70 degrees, which are characteristic of the anatase phase  $TiO_2$  [16].

### TGA results

Initially, the loss of mass for the ash and the amorphous  $SiO_2$  of the Córdoba Region is constant starting at 600 °C and, for the Norte de Santander pair, at 400 °C (Figure 5)

with a total mass loss of 4 and 7 % (of mass) respectively. Based on the FRX elemental analysis, the negative change in mass is due to the loss of water adsorbed in its pores (approximately 2.23 % and 5.23 %). The shape of the curve indicates that the mass loss is gradual but constant, so it can be deduced that the water adsorbed physically into the pores of the material was removed first, and subsequently the loss of chemically bound water or hydroxyl groups begins [26].

In the case of ash from the rice husks, the mineralization of organic-originated carbon may also include the conversion of these composites into carbon dioxide and water. In addition, phosphorus oxides, composed of both  $SiO_2$  and ashes of the rice husk, have a low boiling point (360 °C), so it is deduced that the mass loss includes the volatilization of these oxides. Mercury (II) oxide decomposes at temperatures of 500 °C, so it is also inferred that part of the mass loss is induced by the decomposition of the mercury oxides. Amorphous silica begins to change its crystalline morphology when subjected to temperatures well above 800 °C [27]; consequently, the mass losses of that material presented at this temperature can occur by

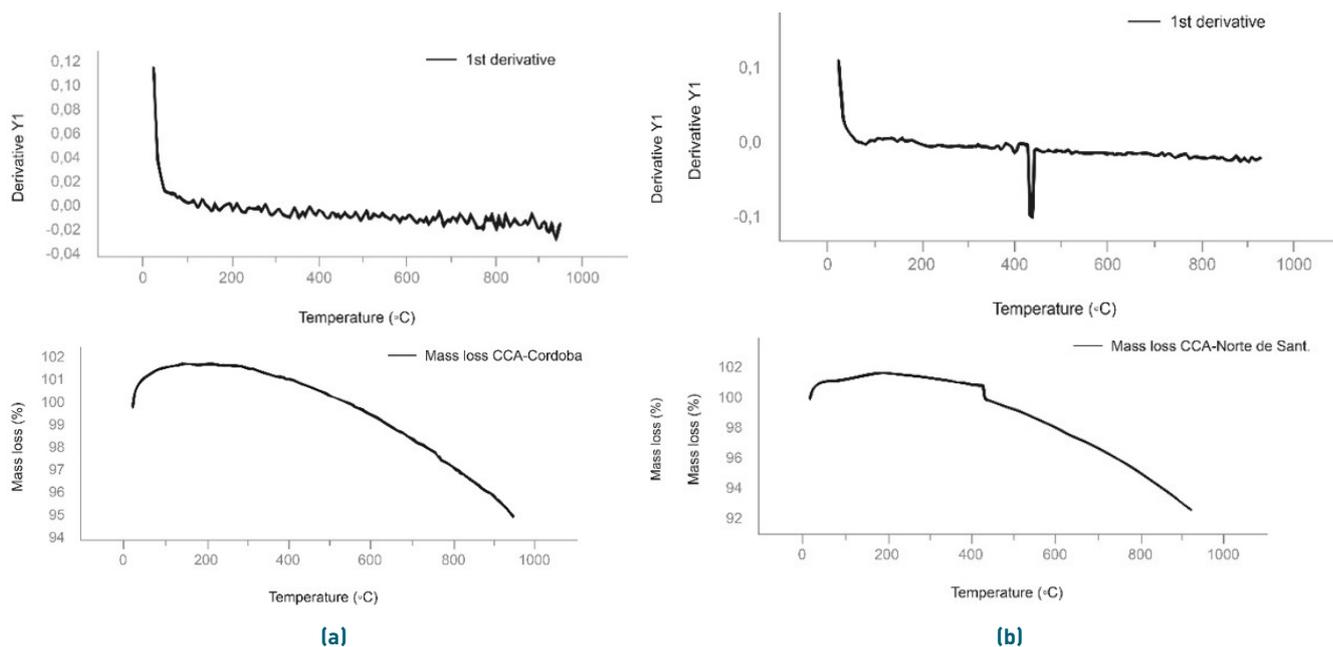

**Figure 5** Thermogravimetric analysis (mass loss curve and first derivative) of CCA from the regions of a. Córdoba; and b. Norte de Santander

the reorganization of the crystalline network of the silica in its transition into quartz crystals or other structures of the crystalline silica [28].

Observing the first derivative of each curve, it can be deduced that the materials have high thermal stability and low reactivity, as well as characteristics of amorphous solids. This analysis shows that the ash and silica obtained are mostly amorphous silica with high chemical and thermal stability [29].

Figure 6 shows the first derivative of the mass loss of the  $SiO_2$  from the Córdoba region, which is related to the thermogravimetric analysis of the other rice husk derivatives obtained for this research work. On the other hand, in the TGA analysis for the composite of mixed oxides, the shape of the thermogram curve reveals a rapid loss of mass of 10 % between 0 °C and 100 °C; it is inferred that this represents the loss of surface moisture (physically adsorbed), which is sustained by observing the first derivative of the mass loss curve. Henceforth, the loss of mass is less pronounced but constant, eventually losing 20 %. This mass loss is due to the elimination of chemically bound water and hydroxyl groups [26, 30]. From the mark of 500 °C there is evidence of decomposition of the mercury oxides present in the material, as described in the FRX analysis. In perspective, the total mass loss is 30 %. By observing the first derivative, it is inferred that the composite has moderate thermal stability; however, mass losses induced by the reorganization of the crystalline structure of the composite are not ruled out [14].


Figure 7 shows the mass loss curve, and the first derivative of the analysis applied to the composite  $TiO_2/SiO_2$ . The change is evident with respect to the other thermogravimetric analysis; for this reason, the synthesis product is checked.

### FTIR results


The amorphous  $SiO_2$  of the Córdoba region sample was chosen for the synthesis of the mixed oxides  $TiO_2/SiO_2$ , since it did not exhibit morphological difference with the  $SiO_2$  of Norte de Santander; consequently, the FTIR analysis was applied only to the silica from Córdoba, to evaluate the change in its morphology.

The  $SiO_2$  spectrum (Figure 8a) shows three prominent peaks, one in the  $1071\text{ cm}^{-1}$  region, which is characteristic of stretching movements of Si-O bonds; another in the  $800\text{ cm}^{-1}$ , which is attributed to symmetrical or stretching movements of the Si-O-Si groups; and the latter in the  $600\text{ cm}^{-1}$  band, which is assigned to the torsion movement in the O groups [31–33].

On the other hand, the spectrogram of the mixed oxides shows three peaks (Figure 8b), in  $1078\text{ cm}^{-1}$ ,  $973\text{ cm}^{-1}$  and  $788\text{ cm}^{-1}$ ; the bands of  $973\text{ cm}^{-1}$  and  $788\text{ cm}^{-1}$  differ from those presented by amorphous silica. This difference is attributed to  $SiO_2$  defects induced by the inclusion of Ti(IV) within the  $SiO_2$  crystal structure. The first corresponds to vibrations in Ti-O-Si bonds; and the

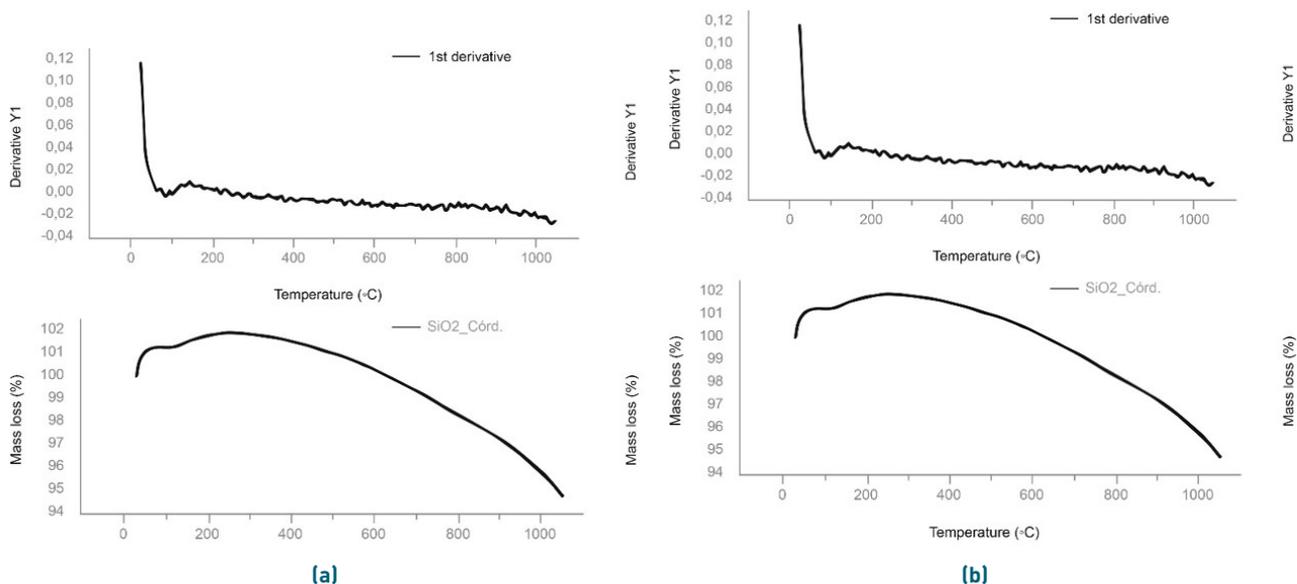

**Figure 6** Thermogravimetric analysis (mass loss curve and first derivative) of silica from CCA a. Córdoba; b. Norte de Santander

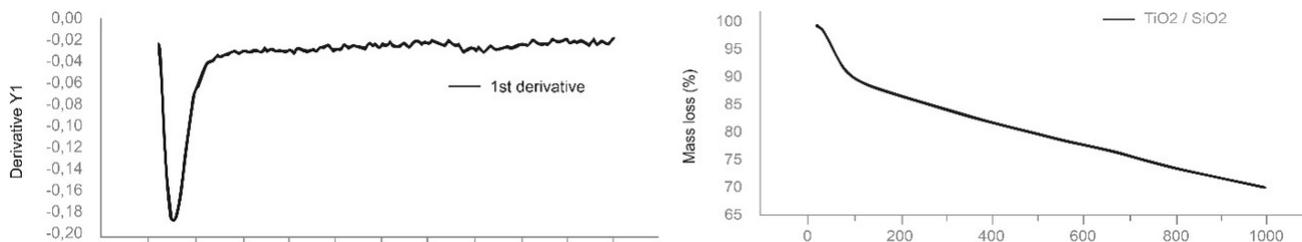

**Figure 7** Thermogravimetric Analysis (mass loss curve and first derivative) composite  $TiO_2/SiO_2$

second, which is accompanied by a wide band, is related to stretching movements in the Ti-O-Ti bonds, characteristic of the anatase phase  $TiO_2$  [16].

**Table 3** Percentage composition of the micrograph points of  $SiO_2$  and  $TiO_2/SiO_2$


Elements (%)	$SiO_2$ Weight (%)	$TiO_2$ - $SiO_2$ Weight (%)
O	62.94	68.01
Si	37.06	12.72
Ti	--	19.27
<b>Total</b>	<b>100.00</b>	100.00

### SEM results


The SEM technique was applied to the amorphous  $SiO_2$  extracted from the CCA from Córdoba and mixed  $TiO_2/SiO_2$  oxide, this technique seeks to analyze the changes in the morphology of the synthesis and the possible inclusion of the Ti(IV) ions inside its structure. In Figure 9a and Figure 9b, obtained by SEM at 40000X, it is observed that the  $SiO_2$  surface has rough features and that there is presence of certain granular-shaped

conglomerates in several sizes. When comparing the results with the micrography of the mixed oxide, it is evident that both materials present equal amorphicity, with very rough particles, which indicates high porosity. Titanium oxide and  $SiO_2$  interacted so that the former adhered to the  $SiO_2$  surface as a support.

The aforementioned interaction was evident when the elemental composition was analyzed by the EDS dispersive energy technique (Table 3), where it can be observed that the composition of the particles is clearly  $SiO_2$ ; while, in the case of the mixed oxide, there is presence of titanium on silica, in contrast with the FTIR analysis. It is deduced that the  $TiO_2$  is indeed supported on the  $SiO_2$ . Finally, in terms of percentages, it is expected that oxygen is present in a greater proportion due to the bonds it forms with titanium and silicon; thus, demonstrating that by using this semiquantitative tool (EDS) there is evidence that the inclusion of the particles occurred, forming Ti-O-Si bonds.

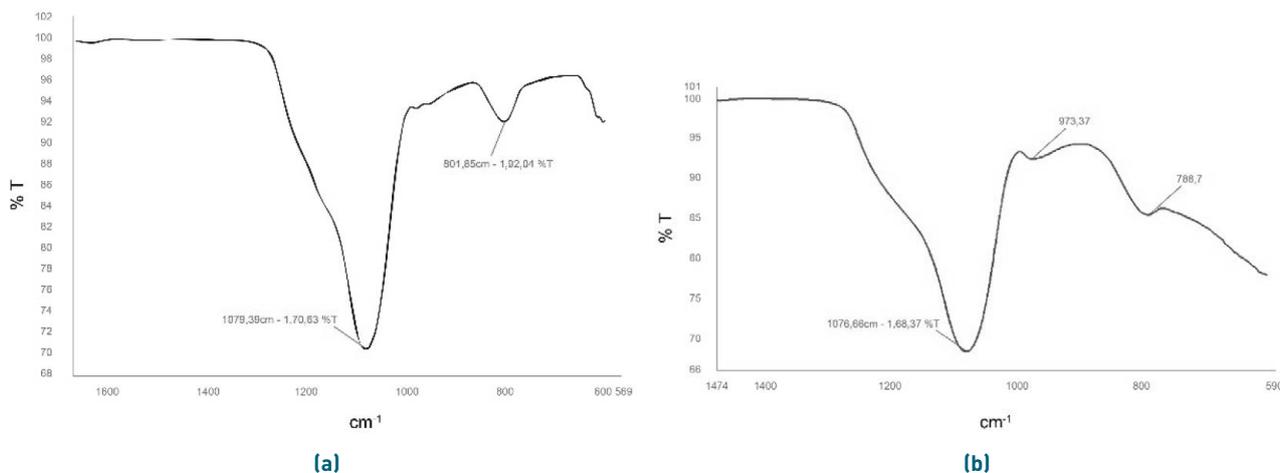

**Figure 8** FTIR spectroscopic analysis: a. Silica from Córdoba region. b. Mixed oxides  $TiO_2/SiO_2$  synthesized

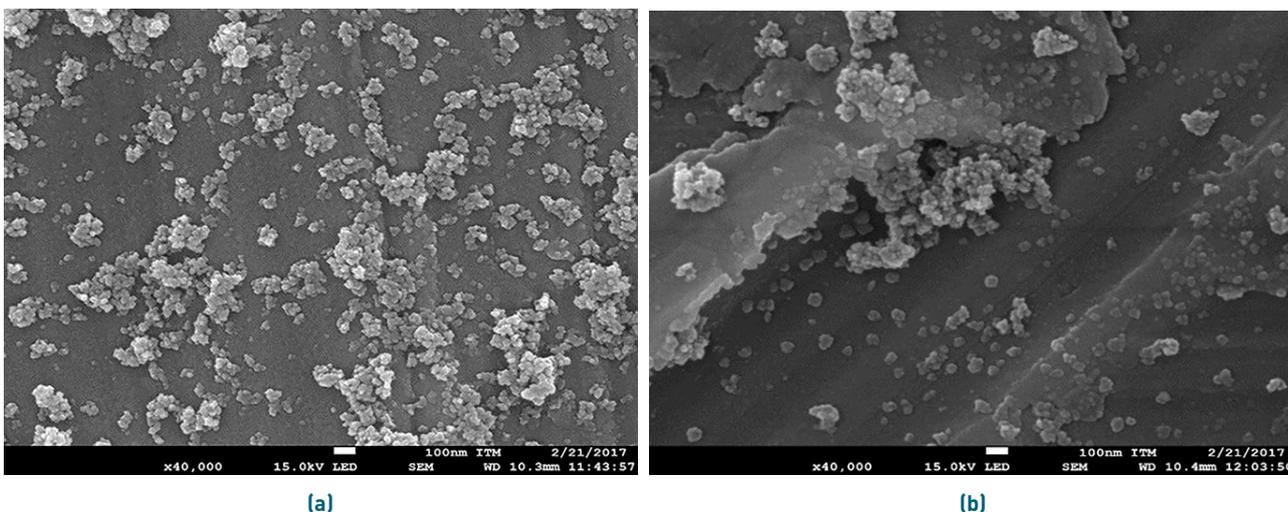

**Figure 9** SEM of a. Córdoba silica and b. mixed oxides taken at 100 nm and magnification of 40000x

## References

- [1] R. Chakraborty, A. Asthana, A. K. Singh, B. Jain, and A. B. H. Susan, "Adsorption of heavy metal ions by various low-cost adsorbents: a review," *Int J Environ Anal Chem*, vol. 102, no. 2, Feb. 20, 2020. [Online]. Available: <https://doi.org/10.1080/03067319.2020.1722811>
- [2] W. Liu, L. Jin, J. Xu, Y. Liu, J. Li, P. Zhou, and *et al.*, "Insight into ph dependent cr(vi) removal with magnetic  $fe_3s_4$ ," *Chemical Engineering Journal*, vol. 359, Nov. 24 2018. [Online]. Available: <https://doi.org/10.1016/j.cej.2018.11.192>
- [3] H. K.-M. A. Ayati, S. Ghanbari, Y. Orooji, B. Tanhaei, F. Karimi, and *et al.*, "Recent advances in removal techniques of cr(vi) toxic ion from aqueous solution: A comprehensive review," *Journal of Molecular Liquids*, vol. 329, May 01, 2021. [Online]. Available: <https://doi.org/10.1016/j.molliq.2020.115062>
- [4] A. K. Priya, V. Yogeshwaran, S. Rajendran, T. K. A. Hoang, M. Soto-Moscoso, A. A. Ghfar, and *et al.*, "Investigation of mechanism of heavy metals [ $cr^{6+}$ ,  $pb^{2+}$  &  $zn^{2+}$ ] adsorption from aqueous medium using rice husk ash: Kinetic and thermodynamic approach," *Chemosphere*, vol. 286, Jan. 2022. [Online]. Available: <https://doi.org/10.1016/j.chemosphere.2021.131796>
- [5] D. Giuranno, S. Gambaro, G. Bruzda, R. Nowak, W. Polkowski, N. Sobczak, and *et al.*, "Interface design in lightweight  $sic/tisi_2$  composites fabricated by reactive infiltration process: Interaction phenomena between liquid si-rich si-ti alloys and glassy carbon," *Materials*, vol. 14, no. 13, 2021. [Online]. Available: <https://doi.org/10.3390/ma14133746>
- [6] Y. Wang, Z. Xing, Z. Li, X. Wu, G. Wang, and W. Zhou, "Facile synthesis of high-thermostably ordered mesoporous  $tio_2/sio_2$  nanocomposites: An effective bifunctional candidate for removing arsenic contaminations," *Journal of Colloid and Interface Science*, vol. 485, Jan. 01, 2017. [Online]. Available: <https://doi.org/10.1016/j.jcis.2016.09.022>
- [7] V. Degiovanni, L. E. Berrio, and R. E. Charry, Eds., *Origen , taxonomía , anatomía y morfología de la planta de arroz (Oryza sativa L .)*, ser. Producción eco-eficiente del arroz en América Latina. Cali, CO: Centro Internacional de Agricultura Tropical (CIAT), 2017. [Online]. Available: <https://cgspace.cgiar.org/bitstream/handle/10568/82462/origen-ff4737f6.pdf?sequence=1>
- [8] V. Degiovanni-Beltramo, J. Gómez, and J. Sierra, "Análisis de crecimiento y etapas de desarrollo de tres variedades de arroz (oryza sativa l.) en montería, córdoba," *Temas Agrarios*, vol. 9, no. 1, Jan-Jun. 2004. [Online]. Available: <https://doi.org/10.21897/rta.v9i1.620>
- [9] H. Memedi, K. Atkovska, K. Lisichkov, M. Marinkovski, S. Kuvendziev,

- Z. Bozinovski, and et al., "Removal of cr(vi) from water resources by using different raw inorganic sorbents," *Quality of Life (Banja Luka) - APEIRON*, vol. 7, no. 3-4, 2016. [Online]. Available: <https://doi.org/10.7251/qol1603077m>
- [10] H. B. Yener and S. S. Helvacı, "Effect of synthesis temperature on the structural properties and photocatalytic activity of  $\text{tio}_2/\text{sio}_2$  composites synthesized using rice husk ash as a  $\text{sio}_2$  source," *Separation and Purification Technology*, vol. 140, Jan. 22, 2015. [Online]. Available: <https://doi.org/10.1016/j.seppur.2014.11.013>
- [11] P. U. Nzereogu, A. D. Omah, F. I. Ezema, E. I. Iwuoha, and A. C. Nwanya, "Silica extraction from rice husk: Comprehensive review and applications," *Hybrid Advances*, vol. 4, Dec. 2023. [Online]. Available: <https://doi.org/10.1016/j.hybadv.2023.100111>
- [12] Y. Wang, C. Peng, E. Padilla-Ortega, A. Robledo-Cabrera, and A. López-Valdivieso, "Cr(vi) adsorption on activated carbon: Mechanisms, modeling and limitations in water treatment," *Journal of Environmental Chemical Engineering*, vol. 8, no. 4, Aug. 2020. [Online]. Available: <https://doi.org/10.1016/j.jece.2020.104031>
- [13] T. Zang, Z. Cheng, L. Lu, Y. Jin, X. Xu, W. Ding, and J. Qu, "Removal of cr(vi) by modified and immobilized *Auricularia auricula* spent substrate in a fixed-bed column," *Ecological Engineering*, vol. 99, Feb. 2017. [Online]. Available: <https://doi.org/10.1016/j.ecoleng.2016.11.070>
- [14] H. Banu-Yener and S. S. Helvacı, "Visible light photocatalytic activity of rutile  $\text{tio}_2$  fiber clusters in the degradation of terephthalic acid," *Applied Physics A*, vol. 120, Jun. 03, 2015. [Online]. Available: <https://doi.org/10.1007/s00339-015-9263-4>
- [15] T. Rasheed, M. Adeel, F. Nabeel, M. Bilal, and H. M. N. Iqbal, " $\text{Tio}_2/\text{sio}_2$  decorated carbon nanostructured materials as a multifunctional platform for emerging pollutants removal," *Science of the Total Environment*, vol. 688, Oct. 20, 2019. [Online]. Available: <https://doi.org/10.1016/j.scitotenv.2019.06.200>
- [16] R. Nandanwar, P. Ingh, F. F. Syed, and F. Z. Haque, "Preparation of  $\text{tio}_2/\text{sio}_2$  nanocomposite with non-ionic surfactants via sol-gel process and their photocatalytic study," *Oriental Journal of Chemistry*, vol. 30, no. 4, 2014. [Online]. Available: <http://dx.doi.org/10.13005/ojc/300417>
- [17] N. F. Jaafar, N. F. Jaafar, M. Khairuddean, and N. Nordin, "A review on recent progression of modifications on titania morphology and its photocatalytic performance," *Acta Chimica Solvenica*, vol. 67, 2020. [Online]. Available: <https://doi.org/10.17344/acsi.2019.5161>
- [18] T. Serrano, M. V. Borrachero, J. M. Monzó, and J. Paya, "Morteros aligerados con cascarilla de arroz: Diseño de mezclas y evaluación de propiedades," *Dyna*, vol. 79, no. 175, Sep-Oct. 2012. [Online]. Available: [http://scielo.org.co/scielo.php?script=sci\\_arttext&pid=S0012-73532012000500015](http://scielo.org.co/scielo.php?script=sci_arttext&pid=S0012-73532012000500015)
- [19] A. T. Ortega-Ramírez, M. Reyes-Tovar, and O. Silva-Marrufo, "Rice husk reuse as a sustainable energy alternative in tolima, colombia," *Scientific Reports*, vol. 14, May. 06, 2024. [Online]. Available: <https://doi.org/10.1038/s41598-024-60115-5>
- [20] M. P. Argumedo-García, A. Consuegra-Solórzano, J. V. Vidal-Durango, and J. L. Marrugo-Negrete, "Exposición a mercurio en habitantes del municipio de san marcos (departamento de sucre) debida a la ingesta de arroz (*oryza sativa*) contaminado," *Revista Salud Pública*, vol. 15, no. 6, Dec. 2013. [Online]. Available: <https://www.scielosp.org/pdf/rsap/v15n6/v15n6a10.pdf>
- [21] C. M. R. Almeida, M. E. Ghica, and L. Durães, "An overview on alumina-silica-based aerogels," *Advances in Colloid and Interface Science*, vol. 282, Aug. 2020. [Online]. Available: <https://doi.org/10.1016/j.cis.2020.102189>
- [22] L. Galeano, J. A. Navío, G. M. Restrepo, and J. M. Marín, "Preparación de sistemas Óxido de titanio/Óxido de silicio [ $\text{tio}_2/\text{sio}_2$ ] mediante el método solvotérmico para aplicaciones en fotocatalisis," *Informacion Tecnologica*, vol. 24, no. 5, 2013. [Online]. Available: <http://dx.doi.org/10.4067/S0718-07642013000500010>
- [23] C. Goncalves-Rocha, D. A. Morozin-Zaia, R. V. da Silva-Alfaya, and A. A. da Silva-Alfaya, "Use of rice straw as biosorbent for removal of cu(ii), zn(ii), cd(ii) and hg(ii) ions in industrial effluents," *Journal of Hazardous Materials*, vol. 166, no. 1, Ju. 15, 2009. [Online]. Available: <https://doi.org/10.1016/j.jhazmat.2008.11.074>
- [24] R. A. Bakar, R. Yahya, and S. N. Gan, "Production of high purity amorphous silica from rice husk," *Procedia Chem.*, vol. 19, Mar. 24, 2016. [Online]. Available: <https://doi.org/10.1016/j.proche.2016.03.092>
- [25] R. M. Mohamed, I. A. Mkhaliid, and M. A. Barakat, "Rice husk ash as a renewable source for the production of zeolite nay and its characterization," *Arabian Journal of Chemistry*, vol. 8, no. 1, jan. 2015. [Online]. Available: <https://doi.org/10.1016/j.arabjc.2012.12.013>
- [26] E. Pabón-Gelves, S. M. Borja-Ordóñez, J. Ordóñez-Loza, and A. Ramírez-Vélez, "Síntesis y caracterización de Óxidos mixtos de sílice-titania preparados por método sol-gel y tratamiento hidrotérmico," *Revista EIA*, vol. 19, Jan-Jun. 2013. [Online]. Available: [http://www.scielo.org.co/scielo.php?pid=S1794-12372013000100011&script=sci\\_arttext](http://www.scielo.org.co/scielo.php?pid=S1794-12372013000100011&script=sci_arttext)
- [27] S. Steven, E. Restiawaty, and Y. Bindar, "Routes for energy and bio-silica production from rice husk: A comprehensive review and emerging prospect," *Renewable and Sustainable Energy Reviews*, vol. 149, Oct. 2021. [Online]. Available: <https://doi.org/10.1016/j.rser.2021.111329>
- [28] L. Pérez-Quiñones, M. Llanes-Pérez, Y. Morales-Rodríguez, U. Tecnológica, D. L. Habana, and J. Antonio, "Availability of  $\text{sio}_2$  from the controlled burning of mayabeque rice shell," *Revista Ciencia y Construcción*, vol. 2, no. 1, Jan-Mar. 2021. [Online]. Available: <https://tinyurl.com/uxmx5rhn>
- [29] F. Peng, Y. Jiang, J. Feng, F. Liu, J. Feng, and L. Li, "Novel silica-modified boehmite aerogels and fiber-reinforced insulation composites with ultra-high thermal stability and low thermal conductivity," *Journal of the European Ceramic Society*, vol. 42, no. 14, Nov. 2022. [Online]. Available: <https://doi.org/10.1016/j.jeurceramsoc.2022.07.001>
- [30] H. G. Palhares, B. S. Gonçalves, L. M. C. Silva, E. H. M. Nunes, and M. Houmard, "Clarifying the roles of hydrothermal treatment and silica addition to synthesize  $\text{tio}_2$ -based nanocomposites with high photocatalytic performance," *Journal of Sol-Gel Science and Technology*, vol. 95, Mar. 25, 2020. [Online]. Available: <https://doi.org/10.1007/s10971-020-05265-4>
- [31] S. A. Abo-El-Enein, M. A. Eissa, A. A. Diafullah, M. A. Rizk, and F. M. Mohamed, "Removal of some heavy metals ions from wastewater by copolymer of iron and aluminum impregnated with active silica derived from rice husk ash," *Journal of Hazardous Materials*, vol. 172, no. 2-3, Dec. 30, 2009. [Online]. Available: <https://doi.org/10.1016/j.jhazmat.2009.07.036>
- [32] Y. Ding and D. Su, "Purifying native in-situ mastoid  $\text{sio}_2$  from rice husk," *Energy Procedia*, vol. 16, no. Part B, Mar. 16, 2012. [Online]. Available: <https://doi.org/10.1016/j.egypro.2012.01.203>
- [33] F. M. Mohamed, K. A. Alfalous, and M. E. Gamal, "Utilization of poly inorganic coagulants impregnated with activated silica derived from rice husk ash in treatment of grey water," *Water, Energy, Food and Environment Journal*, vol. 1, no. 2, May. 2020. [Online]. Available: <http://dx.doi.org/10.18576/wefej/010202>