

# Casein phosphopeptide-amorphous calcium phosphate nanocomplex (CPP-ACP) in dentistry: state of the art

## Nanocomplejo de fosfopéptido de caseína-fosfato de calcio amorfo (CPP-ACP) en Odontología: estado del arte

CRISTHIAN CAMILO MADRID TROCONIS<sup>1</sup>, STEFANIE DEL CARMEN PEREZ PUELLO<sup>2</sup>

<sup>1</sup> Ph.D candidate and Master in Dental Materials, School of Dentistry, State University of Campinas (FOP-UNICAMP), Brazil. Member of dental materials research group, School of Dentistry, University of Cartagena (MADEFOUC), Cartagena, Colombia.

<sup>2</sup> Master in Dentistry (Public Health), School of Dentistry, State University of Campinas (FOP-UNICAMP), Brazil. Professor at Corporación Universitaria Rafael Núñez (CURN), Cartagena, Colombia.

### ABSTRACT

Saliva and external agents containing different concentrations of sodium fluoride (NaF) promote the dental remineralization process. However, these resources may not be sufficient to counteract the multiple factors involved in the process of dental caries, especially in high-risk patients. There are alternatives that have been extensively researched, such as casein phosphopeptide-amorphous calcium phosphate (CPP-ACP) which provides essential ions, like phosphate and calcium, acting as an adjuvant in the remineralization process. Manufacturers of CPP-ACP-based products also suggest that it can produce desensitizing effects. This nanocomplex has been used experimentally with some dental cements and adhesive systems, but it is important to clarify the effects of this procedure, and the remineralizing/desensitizing advantages it offers. The objective of this topic review was to present the state of the art on CPP-ACP nanocomplex. In terms of dental caries prevention, this remineralizing option is not better than NaF. CPP-ACP provides a dental desensitizing action, but it is temporary, similar or less effective than other alternatives such as potassium nitrate or NaF. The experimental incorporation of CPP-ACP into dental cements should be controlled for not to compromise the physico-chemical properties of the material. The use of dental products based on this nanocomplex as dental surface pretreatment may decrease the bond strength of adhesive materials, but this effect is material dependent.

**Keywords:** casein phosphopeptide-amorphous calcium phosphate, dental demineralization, dental remineralization, tooth decay, dentin sensitivity

### RESUMEN

La saliva y agentes externos que contienen diferentes concentraciones de fluoruro de sodio (NaF) favorecen el proceso de remineralización dental. No obstante, estos recursos podrían no ser suficientes para contrarrestar los múltiples factores involucrados en el proceso de caries dental, especialmente en pacientes con alto riesgo. Existen alternativas que han sido ampliamente investigadas, como el fosfopéptido de caseína-fosfato de calcio amorfo (CPP-ACP) que aporta iones esenciales como fosfato y calcio, actuando como coadyuvante en el proceso de remineralización. Los fabricantes de productos basados en CPP-ACP también sugieren que este es capaz de generar efectos desensibilizantes. Este nanocomplejo ha sido utilizado de forma experimental con algunos cementos dentales y sistemas adhesivos, pero es importante esclarecer los efectos de dicha incorporación y las ventajas remineralizantes/desensibilizantes que ofrece esta alternativa. El objetivo del presente artículo de revisión de tema consistió en presentar el estado del arte sobre el nanocomplejo CPP-ACP. En términos de prevención de caries dental, esta opción remineralizante no es superior al NaF. El nanocomplejo ejerce acción desensibilizante dental, pero esta es transitoria, similar o inferior a otras alternativas como nitrato de potasio o NaF. La incorporación experimental de CPP-ACP en cementos dentales debe ser controlada para no comprometer las propiedades físico-químicas del material. La utilización de productos dentales a base de este nanocomplejo como pretratamiento de la superficie dental puede disminuir la resistencia de unión de materiales adhesivos, pero este efecto es material-dependiente.

**Palabras clave:** nanocomplejo de fosfopéptido de caseína-fosfato de calcio amorfo, desmineralización dental, remineralización dental, caries dental, sensibilidad de la dentina

Submitted: March 7/2017 - Accepted: September 11/2018



**How to quote this article:** Madrid Troconis CC, Perez Puello S del C. Casein phosphopeptide-amorphous calcium phosphate nanocomplex (CPP-ACP) in dentistry: state of the art. Rev Fac Odontol Univ Antioq. 2019; 30(2): 248-263. DOI: <http://dx.doi.org/10.17533/udea.rfo.v30n2a10>

## INTRODUCTION

Due to the dynamic conditions of the oral environment, enamel and exposed dentin are subjected to constant fluctuations of temperature, moisture, presence of biofilm and pH changes.<sup>1</sup> The latter two are stimulated by the intake of carbohydrate-rich foods, which promotes the adhesion, proliferation and activity of various cariogenic microorganisms which release acids that reduce dental hydroxyapatite into more soluble apatite. The cumulative effect of the aforementioned alterations and the influence of other factors such as time, reduction of the buffering capacity of saliva, and deficient oral hygiene favor the onset of incipient dental caries lesions.<sup>2,3</sup> However, the oral environment is dynamic and the re-incorporation of lost minerals occurs alternately to the dental demineralization processes with the help of saliva and its contribution of  $\text{Ca}^{2+}$  and  $\text{PO}_4^{3-}$  ions through a complex process called dental remineralization.<sup>4</sup>

Currently, there are several adjuvant methods to speed up this process, prevent and control the progression of incipient carious lesions, also called white spot lesions (WSLs). Sodium fluoride (NaF) is the most commonly used agent and can be supplied systemically through fluoridated water or in common diet foods. It can also be applied topically through toothpastes, mouthwashes or gels/varnishes during dental consultation.<sup>5,6</sup> The bioavailability of NaF in saliva causes its precipitation and stability on dental structure, delaying the demineralization process and promoting dental remineralization process.<sup>7</sup> However, there have been discussions related to its use, due to the low solubility in the presence of  $\text{Ca}^{2+}$  and  $\text{PO}_4^{3-}$  ions in saturated solutions.<sup>1,7</sup> In addition, the rapid deposition of NaF in

the surface layer of the carious lesion limits a deep remineralization.<sup>8</sup> The toxic effects of NaF at high concentrations have been controversial, due to the high risk when taking low doses from multiple sources. In fact, the cumulative effect of NaF during the early stages of life is sufficient to cause dental fluorosis.<sup>9,10</sup>

Another preventive/therapeutic alternative tested in *in vitro*, *in situ* and *in vivo* studies and used in recent years is the casein phosphopeptide-amorphous calcium phosphate nanocomplex (CPP-ACP).<sup>11,12</sup> This nanocomplex is an agent that saturates saliva and biofilm, favoring the dental remineralization process by providing  $\text{Ca}^{2+}$  and  $\text{PO}_4^{3-}$  ions, which then become available, reducing the risk of hard dental tissues demineralization. Modifications to the original nanocomplex have recently been made, incorporating NaF concentrations to enhance its preventive effect. Several studies have compared the remineralizing action of this complex and NaF, traditionally used in the prevention and treatment of initial caries lesions.<sup>13,14</sup>

In addition, manufacturers of CPP-ACP-based products indicate that it produces a desensitizing effect. However, its clinical superiority over other strategies has not been confirmed. Some dental desensitizers are potassium nitrate ( $\text{KNO}_3$ ), fluorides, glutaraldehyde, hydroxyethyl methacrylate (HEMA), arginine-calcium carbonate complex, sodium calcium phosphosilicate (Bioglass 45S5), strontium acetate, oxalate, and laser.<sup>15</sup> Different concentrations of CPP-ACP have been incorporated experimentally into dental materials and used in adhesive laboratory procedures to promote additional benefits to dental structure.<sup>16,17</sup> For these reasons, it is important to know the remineralizing/desensitizing benefits of

CPP-ACP compared to traditional strategies, as well as the products that incorporate this technology and their clinical effectiveness based on evidence. The objective of this topic review was to present the state of the art on the casein phosphopeptide-amorphous calcium phosphate nanocomplex.

## CASEIN PHOSPHOPEPTIDE-AMORPHOUS CALCIUM PHOSPHATE NANOCOMPLEX (CPP-ACP)


CPP-ACP is a nanocomplex patented by Reynolds at the University of Melbourne, Australia.<sup>18</sup> It is made up of the phosphopeptide casein protein (CPP), which is derived from milk and it is structured by residues of phosphorylated serine and glutamic amino acid.<sup>19</sup> In addition, it contains a precursor of dental hydroxyapatite: amorphous calcium phosphate (ACP), whose ions are phosphorylated by the serine residues in CPP.<sup>20</sup> Several studies focus on its remineralizing and dental caries preventive effect.<sup>12-14,16,19</sup> In addition, it has been noted that it produces a desensitizing action,<sup>15</sup> as well as additional bacteriostatic effects.<sup>20</sup>

### The remineralizing effect of CPP-ACP

The remineralizing effect is caused by the stabilization of  $\text{Ca}^{2+}$  and  $\text{PO}_4^{3-}$  ions that are in solution, by binding ACP to multiple amine residues of phosphorylated serine present in CPP. Thus, it enables the formation of nano-sized clusters, also called CPP-ACP nanoclusters, which increases the total surface area, as well as its interaction with biofilm and dental structure. The clusters prevent nucleation and spontaneous precipitation of  $\text{Ca}^{2+}$  ions, and behave like salivary proteins such as estaterin and

other proline-rich proteins.<sup>21</sup> The continued use of dental products containing CPP-ACP produces ion saturation in saliva and biofilm, making it available for subsequent precipitation in the form of ACP, favoring the dental remineralization process (Figure 1).<sup>22-24</sup> Several laboratory studies have suggested that the remineralization process promoted by this nanocomplex decreases surface roughness and improves the micromorphological characteristics of tooth enamel following microabrasion, orthodontic stripping, bracket removal, or erosive processes.<sup>25-27</sup>

Other *in vitro* studies have shown that the remineralizing effect of products containing CPP-ACP nanocomplex is similar to that produced by fluorides.<sup>28,29</sup> However, this superiority has been questioned, as recently shown through the use of laser confocal microscopy to evaluate the remineralizing potential of a fluoride varnish (Fluor Protector; Ivoclar Vivadent), a CPP-ACP-based paste (GC Tooth Mousse, Recaldent; GC Corp; Japan) and another paste based on fTCP (functionalized Tri-Calcium Phosphate) (Clinpro Toothcreme, 3M). The results showed that the fluoride varnish was more effective in decreasing the depth of incipient dental caries lesions, followed by the CPP-ACP-based paste; however, this latter was better than the one containing fTCP.<sup>30</sup> In 2015, Vyavhare et al compared the remineralizing effect of nano-hydroxyapatite (10%), NaF (1,000 ppm), CPP-ACP (10%) and deionized water (negative control) by means of Vickers microhardness and scanning electron microscopy (SEM), demonstrating that the use of nano-hydroxyapatite and NaF significantly increases microhardness and promotes the reduction of superficial defects and porosities on demineralized tooth enamel.<sup>31</sup>

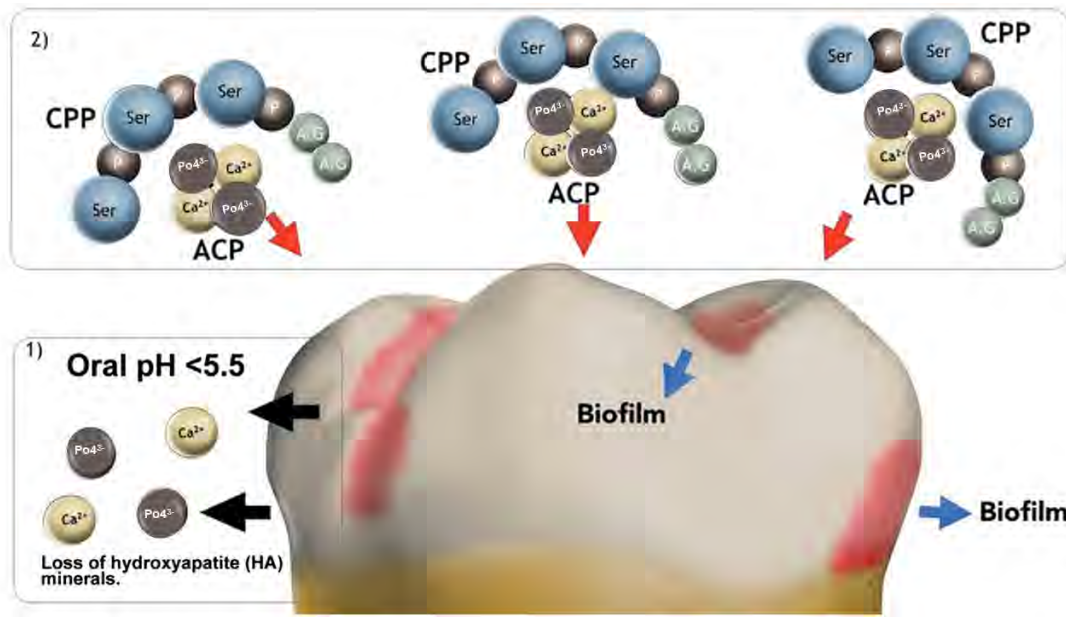

**Figure 1.** Graphic representing the process of dental demineralization/remineralization. 1) Oral pH < 5.5 induces loss of hydroxyapatite (HA) minerals. 2) Saturation of the oral environment and biofilm with Ca<sup>2+</sup> and PO<sub>4</sub><sup>3-</sup> ions, promoting the dental remineralization process.

Source: By the authors

For these reasons, the remineralizing property of NaF has recently been integrated into dental products containing phosphopeptide to form a new complex called CPP-ACPF (casein phosphopeptide-amorphous calcium phosphate fluoride). It should be emphasized that there are no negative interactions between the two components; on the contrary, there is a synergistic effect, providing essential components (PO<sub>4</sub><sup>3-</sup>, Ca<sup>2+</sup>, NaF) to dental structure, which is ideal to promote an integral remineralization process.<sup>32</sup> Evaluations conducted in human enamel by means of Vickers microhardness, SEM and laser fluorescence have shown that remineralizing CPP-ACP-based

pastes that incorporate 0.2% NaF (e.g., MI Paste Plus™ / GC Tooth Mousse-Plus®) increase surface microhardness, decrease the surface irregularities produced by demineralization and form more marked mineral deposits than those generated by pastes that only contain CPP-ACP.<sup>33,34</sup> However, the remineralization of the dental surface is observed only 7 days after starting treatment with Tooth Mousse-Plus®.<sup>35</sup> Currently, there are several dental products that contain CPP-ACP, CPP-ACPF and ACP in different presentations, such as topical pastes, gels, varnishes, xylitol- or sorbitol-based chewing gums, among others (Table 1).<sup>36-38</sup>


**Table 1.** Dental products containing CPP-ACP, CPP-ACPF and ACP

Active ingredients	Trademark (Manufacturer)	Commercial presentation
CPP-ACP	MI Paste™ (GC) / Tooth Mousse™ (GC)	Topical paste
	Trident Xtra Care® (Adams)	Chewing gum
	Trident Total® (Adams)	Chewing gum
	FUJI VII™ EP (GC)	Glass ionomer cement
CPP-ACPF	MI Paste plus™ (GC) / Tooth Mousse plus™ (GC)	Topical paste
	MI Varnish™ (GC)	Varnish
ACP	NiteWhite™ (Phillips)	Tooth bleaching gel
	DayWhite™ (Phillips)	Tooth bleaching gel
	Aegis® Ortho (Bosworth Co)	Dental adhesive
	Aegis® Pit and Fissure Sealant (Bosworth Co)	Pit and fissure sealant
	Relief® ACP (Phillips)	Tooth desensitizing gel
	Enamelon® (Premier)	Toothpaste

## Dental desensitizing mechanism of CPP-ACP

The precipitated  $\text{Ca}^{2+}$  and  $\text{PO}_4^{3-}$  ions from ACP are spread through the phosphorylated fibrils of the exposed intertubular dentin collagen, promoting the formation of apatite.<sup>39</sup> However, both ions are mainly integrated into hypermineralized peritubular dentin, creating deposits at the intratubular

level (Figure 2). This strategy seeks to partially block the external stimuli that influence the hydrodynamic behavior of dentin-pulpal fluid, consequently it decreases dentin hypersensitivity.<sup>40</sup> However, the blocking action in the dentin tubules is partial, similar to that produced by other desensitizing strategies such as the arginine-calcium carbonate complex or strontium acetate.<sup>41</sup>

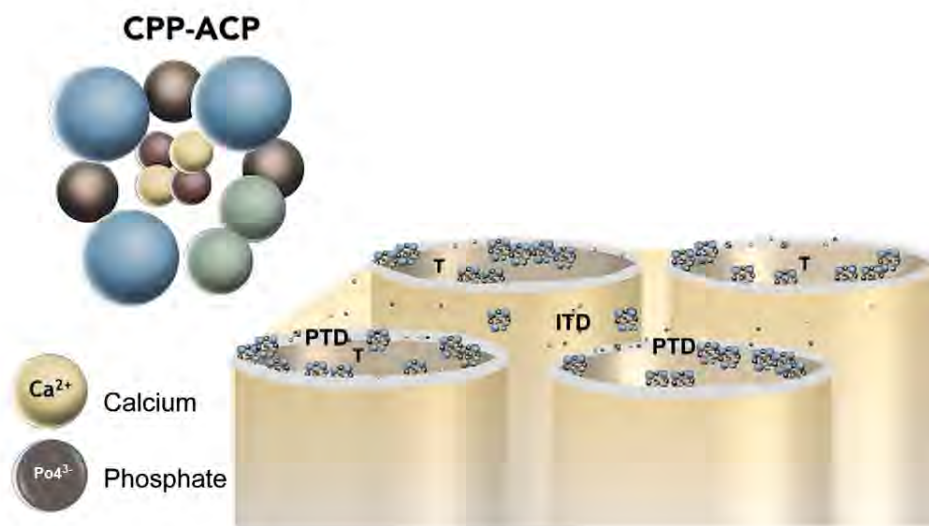

**Figure 2.** Image representing the blocking of exposed dentinal tubules and mineral precipitation from CPP-ACP. T: exposed dentin tubule; PTD: peritubular dentin; ITD: intertubular dentin



The stability of CPP-ACP mineral deposits formed on exposed dentin could be affected by the action of brushing, dietary acids, and phosphatases produced by oral bacteria, causing loss of phosphate groups in the phosphoserines of nanocomplex peptides.<sup>42,43</sup> Therefore, multiple applications of topical dental products incorporating CPP-ACP are needed to promote the formation of significant precipitates of  $\text{Ca}^{2+}$  and  $\text{PO}_4^{3-}$ .

### **Bacteriostatic mechanism of CPP-ACP nanocomplex**

The bacteriostatic mechanism is explained because the nanocomplex is able to bind to the biofilm matrix, saturating it with  $\text{Ca}^{2+}$  and  $\text{PO}_4^{3-}$  ions from ACP.<sup>44</sup> It has been observed that pastes containing CPP-ACP (10%) and glass ionomer cement (GIC) with concentrations of this complex (3%) are able to increase local pH, promoting a neutralizing effect and, masking the receptors of salivary molecules that allow bacterial adhesion. As a result, CPP-ACP slows down growth and decreases the number of colony-forming units of bacteria with high cariogenic potential, such as *Streptococcus mutans*.<sup>45-47</sup> This positive effect was also observed in a short-term clinical study conducted in patients with high risk of dental caries and chronic gingivitis, concluding that the use of a paste based on CPP-ACP reduced the count of bacteria from supragingival plaque and salivary samples, even one month after discontinuing its use.<sup>48</sup>

## **INDICATIONS AND EVIDENCE-BASED CLINICAL EFFECTIVENESS OF CPP-ACP**

### **Dental Caries**

The first visible clinical sign of dental caries is the presence of white spot lesions (WSLs), compatible with demineralization.<sup>49</sup> Several strategies, such as topical fluorides, resin infiltration, and CPP-ACP have been used to achieve regression and improve the aesthetic appearance of these lesions.<sup>50</sup>

In relation to the latter strategy, Memarpour et al (2015) compared the effectiveness of a fluoride varnish (22,600 ppm) (DuraShield; Sultan Healthcare, Hackensack, N.J., USA) with a paste containing CPP-ACP (GC Tooth mousse, Gc, Tokyo, Japan) on WSL regression in 140 children. Measurements of the lesion area and dmft index showed that CPP-ACP paste had a preventive effect similar to the fluoride varnish. However, prolonged use of CPP-ACP decreased the presence of such non-cavitated lesions.<sup>51</sup> Another clinical study conducted by Andersson et al (2007) showed that WSL regression can be achieved using the same CPP-ACP paste or toothpastes containing NaF. Nonetheless, the visual evaluations showed that patients who used CPP-ACP-based paste had better aesthetic results compared to NaF group, possibly related to the presence of other minerals such as calcium and phosphate from ACP which are incorporated to dental structure.<sup>52</sup>

The risk of developing WSLs is also high in patients with fixed orthodontic appliances, because the use of wires, elastics, bands, and brackets hinders correct oral hygiene, favoring biofilm retention.<sup>53,54</sup> In 2011, Brchner et al conducted a controlled clinical trial in 60 adolescents who had at least one WSL following removal of orthodontic appliances. The results from quantitative light-induced fluorescence showed a significant size reduction on incipient dental caries lesions after 4 weeks of using CPP-ACP-containing pastes, improving the clinical aspect of the lesions.<sup>55</sup> A systematic review included 12 controlled clinical studies that evaluated alternatives such as NaF (in vehicles like toothpaste, varnish, and mouthwash) and paste containing CPP-ACP. Overall, the latter proved to be significantly effective in preventing and regressing WSLs.<sup>56</sup>

Another group of patients at high risk of incipient dental caries lesions are those who have degenerative salivary glands diseases, underwent cancer treatment such as chemotherapy, head and neck radiation therapy, or have physical/mental disabilities.<sup>57,58</sup> In this context, an *in situ* study assessed the effectiveness of three remineralizing agents (CPP-ACP, CPP-ACPF and NaF at 0.05%) in Sjogren's syndrome patients. Several relevant aspects related to saliva were evaluated (flow rate, pH, buffering capacity and mineral concentrations), as well as biofilm pH. The study concluded that the use of CPP-ACP and CPP-ACPF caused a slight increase in saliva pH and a significant increase in biofilm pH. In addition, the analysis by energy-dispersive spectroscopy and SEM performed on samples *in situ* showed that the use of these alternatives increased the concentrations of  $\text{Ca}^{2+}$  and  $\text{PO}_4^{3-}$  in the dental surface, and decreased the micromorphological defects of the

enamel surface, which could be of clinical relevance to patients with this condition.<sup>59</sup>

Patients with head and neck cancer undergoing radiation therapy experience non-common dental caries, especially in the cervical, cuspid and incisal levels, characterized by rapid progression and high potential for destruction of dental tissues. Daily use of CPP-ACP and NaF in these patients tend to produce a greater preventive effect against post-radiation caries.<sup>60</sup> However, another study showed that there was no additional positive impact of this nanocomplex in terms of dental caries prevention when associated with a 0.4% stannous fluoride-based gel in patients with nasopharyngeal carcinoma undergoing radiation therapy.<sup>61</sup>

In relation to disabled patients, Zdas et al (2015) conducted a study in cerebral palsy children aged between 3 and 8 years. First, pH measurements were performed on biofilm and saliva buffer capacity was determined. In addition, a CPP-ACP-based paste (GC Tooth mousse, GC, Tokyo, Japan) was applied, evaluating the abovementioned characteristics for a maximum period of 8 weeks. Decreased acidogenicity of biofilm and increased buffering capacity of saliva was observed since the fourth week of treatment.<sup>62</sup> However, there were no comparisons with other remineralizing agents. Clinical evidence on these specific cases is very limited to draw conclusions.

## Dental sensitivity

There are several dental desensitizing strategies such as NaF,  $\text{KNO}_3$  and strontium used in a traditional way. Also, arginine/calcium carbonate complex, bio-active glasses (Bioglass 45s5) and CPP-ACP are being used.<sup>63</sup> In relation to the latter, several

clinical studies have made comparisons with conventional methods. As an example, Mahesuti et al (2014) determined the efficacy of MI Paste™ (GC America, GC, USA) and a KNO<sub>3</sub>-based gel (UltraEZ, Ultradent Products, Inc) in decreasing dentin hypersensitivity levels. The results showed that both dental products were effective but patients treated with KNO<sub>3</sub> experienced decreased pain within two days of treatment, while the group treated with CPP-ACP showed improvements after 7 days.<sup>64</sup> This difference in terms of effectiveness was also reported by Madhavan et al (2012), who compared the effect of a paste containing CPP-ACPF with NaF and propolis after 1, 7, 15, 28, 60 and 90 days, concluding that although all agents reduced the levels of dentin hypersensitivity, patients treated with CPP-ACPF-based paste had to wait more days to experience a significant effect.<sup>65</sup>

It is important to note that the aforementioned cases are characterized by the presence of permeable dentin exposed to the oral environment, which enables the diffusion of KNO<sub>3</sub> up to the nerve endings of deep dentin, or the partial block of dentinal tubules by deposits of Ca<sup>2+</sup> and PO<sub>4</sub><sup>3-</sup>.<sup>64-65</sup> However, patients subjected to dental bleaching with hydrogen peroxide or carbamide-based materials generally feel transient pain during or after treatment, especially when high concentrations of bleaching agents or light sources are used.<sup>66</sup> In these cases, dentin exposure to the oral environment is not necessarily present; therefore, pain has a different etiology and the synergistic effect of desensitizing therapies is required to improve patient experience during esthetic treatment.

Under conditions of transient post-bleaching pain, CPP-ACP-based paste had a desensitizing effect similar to 5% KNO<sub>3</sub> and 0.7% sodium monofluorophosphate after

1 and 7 days as shown in a randomized controlled clinical study.<sup>67</sup> Maghaireh et al (2014) also compared the desensitizing potential of this paste with 2% NaF gel in patients subjected to tooth bleaching using 35% hydrogen peroxide after 1, 3, 7 and 14 days. The study showed that CPP-ACP incorporated in the paste reduced the levels of post-treatment dental pain, but did not present additional therapeutic effects compared to other strategies.<sup>68</sup> However, this desensitizing action in transient post-whitening pain was not observed in patients using xylitol-based chewing gums containing CPP-ACP (at lower concentration: 0.6%), compared with conventional chewing gums.<sup>69,70</sup>

There are tooth bleaching materials such as DayWhite™ and Nitewhite™ that include ACP in their chemical composition. When comparing the desensitizing effectiveness of Nitewhite and other material based on 15% carbamide peroxide, KNO<sub>3</sub> and fluoride, there were no differences in pain levels between both treatments.<sup>71</sup> In general, results from clinical studies suggest that CPP-ACP-based dental products (especially pastes) have a desensitizing effect; however, it does not appear to be higher than other strategies, like KNO<sub>3</sub> or NaF.

## CPP-ACP AND DENTAL MATERIALS

### Interaction between the CPP-ACP nanocomplex and dental bleaching materials

Besides the sensitivity experienced during and after dental bleaching, another relevant topic is related to possible interaction with agents or compounds present in dental structure, different from pigments.



In this specific case, some *in vitro* studies suggest that the action of CPP-ACP-based dental products does not interfere with the oxidation-reduction reactions (redox) generated between the bleaching agent and the structure of chromophores responsible for dental pigmentations; in consequence, CPP-ACP does not affect the aesthetic result of tooth bleaching.<sup>72,73</sup> Another therapeutic alternative to in-office dental bleaching is the application of gases with hyperoxidizing potentials such as ozone (O<sub>3</sub>), which represents an allotropic form of oxygen (O<sub>2</sub>). However, by means of the spectrophotometric values of Delta L\* (lightness difference), Delta A\* (red-green difference) and Delta E (total color difference), it has been confirmed that the concomitant use of a CPP-ACP-based paste during dental bleaching does not affect the oxidizing potential of O<sub>3</sub>.<sup>74</sup>

### The CPP-ACP nanocomplex and the mechanical properties of water-based dental cements

The remineralizing properties of glass ionomer cements (GICs) on demineralized dental regions have been widely reported in the literature.<sup>75,76</sup> However, comparing the remineralization patterns of both options, it has been found that GICs act only on the surface of dental caries lesions, while CPP-ACP-based pastes could remineralize the entire body.<sup>16</sup> Therefore, an *in vitro* study added various concentrations of CPP-ACP into a GIC, specifying that such incorporation must be controlled because concentrations higher than 8% extend the setting time, a factor that can affect the clinical use of this material.<sup>77</sup> Nevertheless, another *in vitro* study showed that the addition of 1.56% (in weight) of CPP-ACP into a GIC increased the material's tensile and compressive strength.<sup>78</sup> Under experimental conditions,

this remineralizing nanocomplex has also been incorporated into temporary eugenol zinc oxide-based cements (Freegenol™ and Temp-Bond® NE) at various concentrations. Similarly, it has been shown that there is a directly proportional relationship between the added percentage and the negative effect on some of their physical and chemical properties, such as solubility and tensile/compressive strength.<sup>79</sup>

### The CPP-ACP nanocomplex and adhesion to dental structure

The CPP-ACP nanocomplex has been used in several experimental *in vitro* protocols as dental surface treatment prior to the application of adhesive materials.<sup>16,17</sup> Clinically, this seeks to seal dentin tubules, reduce post-operative sensitivity and promote the remineralization of previously demineralized dentin or enamel, through the addition of ions provided by ACP. Nonetheless, mineral deposits on dental surface could lead to negative effects on the adhesive interface, as shown by Adebayo et al (2010), who observed microscopic defects in the adhesive interface when a one-step self-etching adhesive was used on dentin previously treated with a CPP-ACP-based paste. On the contrary, these micromorphological alterations were not observed when a two-steps self-etching adhesive was applied.<sup>17</sup>

It is important to note that there is a direct relationship between the characteristics of the adhesive interface and bond strength values of these materials on dental hard tissues. Several studies have shown that prior application of pastes incorporating the remineralizing nanocomplex does not affect the bond strength of etch-and-rinse or two-steps self-etching adhesive systems on dentin affected

by dental caries and sound dentin/enamel.<sup>80-84</sup> However, when one-step self-etching adhesive systems are applied to enamel previously treated with CPP-ACP, the bond strength values of these simplified adhesive materials are significantly reduced.<sup>85</sup> This fact can be explained because the mineral deposits of ACP on the enamel structure cannot be easily modified by the acidic functional monomers contained in one-step self-etching adhesive systems and consequently hinder the interaction and binding to this structure. Nonetheless, a different situation occurs with two steps self-etching and etch-and-rinse adhesive systems.<sup>85-87</sup> The use of phosphoric acid promotes the formation of considerable micromorphological alterations for mineral deposits and the micromechanical interlocking of adhesive systems, without decreasing bond strength values.<sup>85,87</sup>

In general, *in vitro* evidence shows that the effects of using CPP-ACP prior to adhesive systems are material-dependent, with a higher tendency to keep the bond strength of etch-and-rinse adhesive systems and impair the behavior of one-step self etching adhesive systems due to the reaction of the functional monomer phosphoric radical with the cations released by the agglomerates. A similar mechanical impact has been observed when comparing conventional and self-etching resin cements, but the available evidence on the influence of CPP-ACP into these luting materials is still very limited.<sup>88</sup>

## CONCLUSIONS

- The use of dental products incorporating CPP-ACP has a preventive potential for

dental caries, but this potential is not higher than sodium fluoride. However, there is a greater tendency to regression of enamel white spot lesions when products containing CPP-ACP or CPP-ACPF are used.

- The dental desensitizing effect promoted by CPP-ACP or CPP-ACPF-based products is transient, similar or less effective than other strategies.
- The experimental incorporation of CPP-ACP into dental cements should be controlled for not to affect the physical-chemical properties of the material.
- The CPP-ACP pre-treatment impact on the bond strength of adhesive systems to enamel and dentin is material-dependent.

## CONFLICT OF INTEREST

The authors declare that they have no conflict of interest, nor commercial relationships that could trigger commitments or responsibilities in the development of this review.

## CORRESPONDING AUTHOR

Cristhian Camilo Madrid Troconis  
Facultad de Odontología. Universidad  
Estadual de Campinas (FOP-UNICAMP)  
(+5519) 9 83 97 01 77  
cristhianc100@hotmail.com  
Avenida Limeira- 901, Piracicaba,  
CEP: 13414-903  
S o Paulo, Brasil

## REFERENCES

1. Rošin-Grget K, Peroš K, Sutej I, Bašić K. The cariostatic mechanisms of fluoride. *Acta Med Acad.* 2013; 42(2): 179-88. DOI: <https://doi.org/10.5644/ama2006-124.85>
2. Takahashi N, Nyvad B. Caries ecology revisited: microbial dynamics and the caries process. *Caries Res.* 2008; 42(6): 409-18. DOI: <https://doi.org/10.1159/000159604>
3. Strużycka I. The oral microbiome in dental caries. *Pol J Microbiol.* 2014; 63(2): 127-35
4. Dogra S, Bhayya D, Arora R, Singh D, Thakur D. Evaluation of physio-chemical properties of saliva and comparison of its relation with dental caries. *J Indian Soc Pedod Prev Dent.* 2013; 31(4): 221-24. DOI: <https://doi.org/10.4103/0970-4388.121816>
5. Ccahuana-V squez RA, Cury JA. S. mutans biofilm model to evaluate antimicrobial substances and enamel demineralization. *Braz Oral Res.* 2010; 24(2): 135-41
6. Takeuchi R, Kawamura K, Kawamura S, Endoh M, Tomiki S, Taguchi C et al. Effect of school-based fluoride mouth-rinsing on dental caries incidence among schoolchildren in the Kingdom of Tonga. *J Oral Sci.* 2012; 54(4): 343-47
7. Cury JA, Tenuta LM. How to maintain a cariostatic fluoride concentration in the oral environment. *Adv Dent Res.* 2008; 20(1): 13-6. DOI: <https://doi.org/10.1177/154407370802000104>
8. Inkielewicz-Stepniak I, Santos-Martinez MJ, Medina C, Radomski MW. Pharmacological and toxicological effects of co-exposure of human gingival fibroblasts to silver nanoparticles and sodium fluoride. *Int J Nanomedicine.* 2014; 2(9): 1677-87. DOI: <https://dx.doi.org/10.2147%2FIJN.S59172>
9. Whelton HP, Ketley CE, McSweeney F, O'Mullane DM. A review of fluorosis in the European Union: prevalence, risk factors and aesthetic issues. *Community Dent Oral Epidemiol.* 2004; 32 (Suppl 1): 9-18. DOI: <https://doi.org/10.1111/j.1600-0528.2004.00134.x>
10. Azevedo MS, Goettens ML, Torriani DD, Demarco FF. Factors associated with dental fluorosis in school children in southern Brazil: a cross-sectional study. *Braz Oral Res.* 2014; 28(1): 1-7
11. Bayram M, Kusgoz A, Yesilyurt C, Nur M. Effects of casein phosphopeptide-amorphous calcium phosphate application after interproximal stripping on enamel surface: an in-vivo study. *Am J Orthod Dentofacial Orthop.* 2017; 151(1): 167-73. DOI: <https://doi.org/10.1016/j.ajodo.2016.06.033>
12. Bajaj M, Poornima P, Praveen S, Nagaveni NB, Roopa KB, Neena IE et al. Comparison of CPP-ACP, tri-calcium phosphate and hydroxyapatite on remineralization of artificial caries like lesions on primary enamel: an in vitro study. *J Clin Pediatr Dent.* 2016; 40(5): 404-9. DOI: <https://doi.org/10.17796/1053-4628-40.5.404>
13. Pulido MT, Wefel JS, Hernandez MM, Denehy GE, Guzman-Armstrong S, Chalmers JM, et al. The inhibitory effect of MI paste, fluoride and a combination of both on the progression of artificial caries-like lesions in enamel. *Oper Dent.* 2008; 33(5): 550-55. DOI: <https://doi.org/10.2341/07-136>
14. G çl ZA, Alaçam A, Coleman NJ. A 12-week assessment of the treatment of white spot lesions with CPP-ACP paste and/or fluoride varnish. *Biomed Res Int.* 2016; 2016: 8357621. DOI: <https://doi.org/10.1155/2016/8357621>
15. Miglani S, Aggarwal V, Ahuja B. Dentin hypersensitivity: recent trends in management. *J Conserv Dent.* 2010; 13(4): 218-24. DOI: <https://doi.org/10.4103/0972-0707.73385>

16. Thepyou R, Chanmitkul W, Thanatvarakorn O, Hamba H, Chob-Isara W, Trairatvorakul C et al. Casein phosphopeptide-amorphous calcium phosphate and glass ionomer show distinct effects in the remineralization of proximal artificial caries lesion in situ. *Dent Mater J*. 2013; 32(4): 648-65
17. Adebayo OA, Burrow MF, Tyas MJ. Resin-dentine interfacial morphology following CPP-ACP treatment. *J Dent*. 2010; 38(2): 96-105. DOI: <https://doi.org/10.1016/j.jdent.2009.09.007>
18. Reynolds EC. Remineralization of enamel subsurface lesions by casein phosphopeptide-stabilized calcium phosphate solutions. *J Dent Res*. 1997; 76(9): 1587-95. DOI: <https://doi.org/10.1177/00220345970760091101>
19. Meyer-Lueckel H, Wierichs RJ, Schellwien T, Paris S. Remineralizing efficacy of a CPP-ACP cream on enamel caries lesions in situ. *Caries Res*. 2015; 49(1): 56-62. DOI: <https://doi.org/10.1159/000363073>
20. Nongonierma AB, Fitzgerald RJ. Biofunctional properties of casein phosphopeptides in the oral cavity. *Caries Res*. 2012; 46(3): 234-67. DOI: <https://doi.org/10.1159/000338381>
21. Cochrane NJ, Reynolds EC. Calcium phosphopeptides – mechanisms of action and evidence for clinical efficacy. *Adv Dent Res*. 2012; 24(2): 41-47. DOI: <https://doi.org/10.1177/0022034512454294>
22. Shen P, Manton DJ, Cochrane NJ, Walker GD, Yuan Y, Reynolds C et al. Effect of added calcium phosphate on enamel remineralization by fluoride in a randomized controlled in situ trial. *J Dent*. 2011; 39(7): 518-25. DOI: <https://doi.org/10.1016/j.jdent.2011.05.002>
23. Hegde AM, Naik N, Kumari S. Comparison of salivary calcium, phosphate and alkaline phosphatase levels in children with early childhood caries after administration of milk, cheese and GC tooth mousse: an in vivo study. *J Clin Pediatr Dent*. 2014; 38(4): 318-25
24. Cross KJ, Huq NL, Reynolds EC. Casein phosphopeptides in oral health, chemistry and clinical applications. *Curr Pharm Design*. 2007; 13(8): 793-800
25. Mathias J, Kavitha S, Mahalaxmi S. A comparison of surface roughness after micro abrasion of enamel with and without using CPP-ACP: an in vitro study. *J Conserv Dent*. 2009; 12(1): 22-25
26. Giulio AB, Matteo Z, Serena IP, Silvia M, Luigi C. In vitro evaluation of casein phosphopeptide-amorphous calcium phosphate (CPP-ACP) effect on stripped enamel surfaces. A SEM investigation. *J Dent*. 2009; 37(3): 228-32. DOI: <https://doi.org/10.1016/j.jdent.2008.11.015>
27. Mayne RJ, Cochrane NJ, Cai F, Woods MG, Reynolds EC. In-vitro study of the effect of casein phosphopeptide amorphous calcium fluoride phosphate on iatrogenic damage to enamel during orthodontic adhesive removal. *Am J Orthod Dentofacial Orthop*. 2011; 139(6): e543-51. DOI: <https://doi.org/10.1016/j.ajodo.2010.09.027>
28. Lata S, Varghese NO, Varughese JM. Remineralization potential of fluoride and amorphous calcium phosphate-casein phosphopeptide on enamel lesions: an in vitro comparative evaluation. *J Conserv Dent*. 2010; 13(1): 42-6. DOI: <https://doi.org/10.4103/0972-0707.62634>
29. Oliveira GM, Ritter AV, Heymann HO, Swift E Jr, Donovan T, Brock G et al. Remineralization effect of CPP-ACP and fluoride for white spot lesions in vitro. *J Dent*. 2014; 42(12): 1592-602
30. Chokshi K, Chokshi A, Konde S, Shetty SR, Chandra KN, Jana S et al. An in vitro comparative evaluation of three remineralizing agents using confocal microscopy. *J Clin Diagn Res*. 2016; 10(6): 39-42. DOI: <https://doi.org/10.7860/JCDR/2016/18191.7984>
31. Vyavhare S, Sharma DS, Kulkarni VK. Effect of three different pastes on remineralization of initial enamel lesion: an in vitro study. *J Clin Pediatr Dent*. 2015; 39(2): 149-60

32. Srinivasan N, Kavitha M, Loganathan SC. Comparison of the remineralization potential of CPP-ACP and CPP-ACP with 900 ppm fluoride on eroded human enamel: An in situ study. *Arch Oral Biol.* 2010; 55(7): 541-44. DOI: <https://doi.org/10.1016/j.archoralbio.2010.05.002>
33. Shetty S, Hedge MN, Bopanna TP. Enamel remineralization assessment after treatment with three different remineralizing agents using surface microhardness: An in vitro study. *J Conserv Dent.* 2014; 17(1): 49-52. DOI: <https://doi.org/10.4103/0972-0707.124136>
34. Jayarajan J, Janardhanam P, Jayakumar P, Deepika. Efficacy of CPP-ACP and CPP-ACPF on enamel remineralization—an in vitro study using scanning electron microscope and DIAGNOdent. *Indian J Dent Res.* 2011; 22(1): 77-82. DOI: <https://doi.org/10.4103/0970-9290.80001>
35. Patil N, Choudhari S, Kulkarni S, Joshi SR. Comparative evaluation of remineralizing potential of three agents on artificially demineralized human enamel: an in vitro study. *J Conserv Dent.* 2013; 16(2): 116-20. DOI: <https://doi.org/10.4103/0972-0707.108185>
36. Somasundaram P, Vimala N, Mandke LG. Protective potential of casein phosphopeptide amorphous calcium phosphate containing paste on enamel surfaces. *J Conserv Dent.* 2013; 16(2): 152-56. DOI: <https://doi.org/10.4103/0972-0707.108199>
37. Cochrane NJ, Shen P, Yuan, Y, Reynolds EC. Ion release from calcium and fluoride containing dental varnishes. *Aust Dent J.* 2014; 59(1): 100-5. DOI: <https://doi.org/10.1111/adj.12144>
38. De Alencar CR, Magalhães AC, de Andrade Moreira Machado MA, de Oliveira TM, Honório HM, Rios D. In situ effect of a commercial CPP-ACP chewing gum on the human enamel initial erosion. *J Dent.* 2014; 42(11): 1502-07. DOI: <https://doi.org/10.1016/j.jdent.2014.08.008>
39. Cao Y, Mei ML, Xu J, Lo EC, Li Q, Chu CH. Biomimetic mineralisation of phosphorylated dentine by CPP-ACP. *J Dent.* 2013; 41(9): 818-25. DOI: <https://doi.org/10.1016/j.jdent.2013.06.008>
40. Brannstrom M. The hydrodynamic theory of dentinal pain: sensation in preparations, caries, and the dentinal crack syndrome. *J Endod.* 1986; 12(10): 453-57. DOI: [https://doi.org/10.1016/S0099-2399\(86\)80198-4](https://doi.org/10.1016/S0099-2399(86)80198-4)
41. Li R, Li Y, Chen J, Zhou Z, Morrison BM Jr, Panagakos FS. Efficacy of a desensitizing toothpaste containing arginine and calcium carbonate on dentin surface pore structure and dentin morphology. *Am J Dent.* 2012; 25(4): 210-14
42. Gandolfi MG, Silvia F, H PD, Gasparotto G, Carlo P. Calcium silicate coating derived from Portland cement as treatment for hypersensitive dentine. *J Dent.* 2008; 36(8): 565-78. DOI: <https://doi.org/10.1016/j.jdent.2008.03.012>
43. Wang Z, Ma X, Jiang T, Wang Y, Feng Y, Li R. The dentin tubule occlusion effects of desensitizing agents and the stability against acids and brushing challenges. *Am J Dent.* 2015; 28(3): 128-32
44. Rahiotis C, Vougiouklakis G, Eliades G. Characterization of oral films formed in the presence of a CPP-ACP agent: an in situ study. *J Dent.* 2008; 36(4): 272-80. DOI: <https://doi.org/10.1016/j.jdent.2008.01.005>
45. Caruana PC, Mulaify SA, Moazzez R, Bartlett D. The effect of casein and calcium containing paste on plaque pH following a subsequent carbohydrate challenge. *J Dent.* 2009; 37(7): 522-6. DOI: <https://doi.org/10.1016/j.jdent.2009.03.010>
46. Erdem AP, Sepet E, Avshalom T, Gutkin V, Steinberg D. Effect of CPP-ACP and APF on streptococcus mutans biofilm: a laboratory study. *Am J Dent.* 2011; 24(2): 119-23
47. Dashper SG, Catmull DV, Liu SW, Myroforidis H, Zaluzniak I, Palamara JE et al. Casein phosphopeptide-amorphous calcium phosphate reduces streptococcus mutans biofilm development on glass ionomer



- cement and disrupts established biofilms. *PLoS One*. 2016; 11(9): e0162322. DOI: <https://doi.org/10.1371/journal.pone.0162322>
48. Sakr AK, El Karargy AA, Sherif MM. A short-term clinical study on antimicrobial effects of recalcident (CPP-ACP). *Dent Mater*. 2009; 25(5): 11-2. DOI: <http://dx.doi.org/10.1016/j.dental.2009.01.021>
  49. Ekstrand KR, Ricketts DN, Kidd EA. Occlusal caries: pathology, diagnosis and logical management. *Dent Update*. 2001; 28(8): 380-87. DOI: <https://doi.org/10.12968/denu.2001.28.8.380>
  50. Abdullah Z, John J. Minimally invasive treatment of white spot lesions: a systematic review. *Oral Health Prev Dent*. 2016; 14(3): 197-205. DOI: <https://doi.org/10.3290/j.ohpd.a35745>
  51. Memarpour M, Fakhraei E, Dadaein S, Vossoughi M. Efficacy of fluoride varnish and casein phosphopeptide-amorphous calcium phosphate for remineralization of primary teeth: a randomized clinical trial. *Med Princ Pract*. 2015; 24(3): 231-37. DOI: <https://doi.org/10.1159/000379750>
  52. Andersson A, Sköld-Larsson K, Hallgren A, Petersson LG, Twetman S. Effect of a dental cream containing amorphous cream phosphate complexes on white spot lesion regression assessed by laser fluorescence. *Oral Health Prev Dent*. 2007; 5(3): 229-33
  53. Lucchese A, Gherlone E. Prevalence of white-spot lesions before and during orthodontic treatment with fixed appliances. *Eur J Orthod*. 2013; 35(5): 664-68. DOI: <https://doi.org/10.1093/ejo/cjs070>
  54. Enaia M, Bock N, Ruf S. White-spot lesions during multibracket appliance treatment: a challenge for clinical excellence. *Am J Orthod Dentofacial Orthop*. 2011; 140(1): e17-24. DOI: <https://doi.org/10.1016/j.ajodo.2010.12.016>
  55. Brchner A, Christensen C, Kristensen B, Tranæus S, Karlsson L, Sonnesen L et al. Treatment of post-orthodontic white spot lesions with casein phosphopeptide-stabilised amorphous calcium phosphate. *Clin Oral Investig*. 2011; 15(3): 369-73. DOI: <https://doi.org/10.1007/s00784-010-0401-2>
  56. Lopatiene K, Borisovaite M, Lapenaite E. Prevention and treatment of white spot lesions during and after treatment with fixed orthodontic appliances: a systematic literature review. *J Oral Maxillofac Res*. 2016; 7(2): e1. DOI: <https://doi.org/10.5037/jomr.2016.7201>
  57. Carr AJ, Ng WF, Figueiredo F, Macleod RI, Greenwood M, Staines K. Sjögren's syndrome—an update for dental practitioners. *Br Dent J*. 2012; 213(7): 353-57. DOI: <https://doi.org/10.1038/sj.bdj.2012.890>
  58. Hong CH, Napeñas JJ, Hodgson BD, Stokman MA, Mathers-Stauffer V, Elting LS et al. A systematic review of dental disease in patients undergoing cancer therapy. *Support Care Cancer*. 2010; 18(8): 1007-21. DOI: <https://doi.org/10.1007/s00520-010-0873-2>
  59. Peric T, Markovic D, Petrovic B, Radojevic V, Todorovic T, Radicevic BA et al. Efficacy of pastes containing CPP-ACP and CPP-ACPF in patients with Sjögren's syndrome. *Clin Oral Investig*. 2015; 19(9): 2153-65. DOI: <https://doi.org/10.1007/s00784-015-1444-1>
  60. Katsura K, Soga M, Abe E, Matsuyama H, Aoyama H, Takafumi Hayashi T. Effects of casein phosphopeptide-amorphous calcium phosphate with sodium fluoride on root surface conditions in head and neck radiotherapy patients. *Oral Radiol*. 2016; 32: 105-10. DOI: <https://doi.org/10.1007/s11282-015-0218-4>
  61. Sim CP, Wee J, Xu Y, Cheung YB, Soong YL, Manton DJ. Anti-caries effect of CPP-ACP in irradiated nasopharyngeal carcinoma patients. *Clin Oral Investig*. 2015; 19(5): 1005-11. DOI: <https://doi.org/10.1007/s00784-014-1318-y>
  62. Özdas D, Tuna EB, Yilmaz EY, Aytepe Z. Casein phosphopeptide-amorphous calcium phosphate (CPP-ACP) may be an alternative preventive therapy in children with cerebral palsy. *Oral Health Prev Dent*. 2015; 13(5): 11-27. DOI: <https://doi.org/10.3290/j.ohpd.a33090>

63. Davari A, Ataei E, Assarzadeh H. Dentin hypersensitivity: etiology, diagnosis and treatment: a literature review. *J Dent (Shiraz)*. 2013; 14(3): 136-45
64. Mahesuti A, Duan YL, Wang G, Cheng XR, Matis BA. Short-term efficacy of agents containing KNO<sub>3</sub> or CPP-ACP in treatment of dentin hypersensitivity. *Chin J Dent Res*. 2014; 17(1): 43-47
65. Madhavan S, Nayak M, Shenoy, Shetty R, Prasad K. Dentinal hypersensitivity: a comparative clinical evaluation of CPP-ACP F, sodium fluoride, propolis, and placebo. *J Conserv Dent*. 2012; 15(4): 315-18
66. He LB, Shao MY, Tan K, Xu X, Li JY. The effects of light on bleaching and tooth sensitivity during in-office vital bleaching: a systematic review and meta-analysis. *J Dent*. 2013; 40(8): 644-53. DOI: <https://doi.org/10.1016/j.jdent.2012.04.010>
67. Nanjundasetty JK, Ashrafulla M. Efficacy of desensitizing agents on postoperative sensitivity following an in-office vital tooth bleaching: a randomized controlled clinical trial. *J Conserv Dent*. 2016; 19(3): 207-11. DOI: <https://doi.org/10.4103/0972-0707.181927>
68. Maghaireh G, Alzraikat H, Guidoum A. Assessment of the effect of casein phosphopeptide- amorphous calcium phosphate on postoperative sensitivity associated with in-office vital tooth whitening. *Oper Dent*. 2014; 39(3): 239-47. DOI: <https://doi.org/10.2341/12-527-C>
69. Henry RK, Carkin M. The effect of gum chewing on sensitivity associated with in-office whitening procedures. *Int J Dent Hyg*. 2015; 13(4): 308-14. DOI: <https://doi.org/10.1111/idh.12136>
70. Tang B, Millar BJ. Effect of chewing gum on tooth sensitivity following whitening. *Br Dent J*. 2010; 208(12): 571-7. DOI: <https://doi.org/10.1038/sj.bdj.2010.500>
71. Matis BA, Cochran MA, Eckert GJ, Matis JL. In vivo study of two carbamide peroxide gels with different desensitizing agents. *Oper Dent*. 2007; 32(6): 549-55. DOI: <https://doi.org/10.2341/07-10>
72. Cunha AG, De Vasconcelos AA, Borges BC, Vitoriano O, Alves-Junior C, Machado CT et al. Efficacy of in-office bleaching techniques combined with the application of a casein phosphopeptide-amorphous calcium phosphate paste at different moments and its influence on enamel surface properties. *Microsc Res Tech*. 2012; 75(8): 1019-25. DOI: <https://doi.org/10.1002/jemt.22026>
73. Borges BC, Borges JS, de Melo CD, Pinheiro IV, Santos AJ, Braz R et al. Efficacy of a novel at-home bleaching technique with carbamide peroxides modified by CPP-ACP and its effect on the microhardness of bleached enamel. *Oper Dent*. 2011; 36(5): 521-28. DOI: <https://doi.org/10.2341/11-013-L>
74. Manton DJ, Bhide R, Hopcraft MS, Reynolds EC. Effect of ozone and tooth mousse on the efficacy of peroxide bleaching. *Aust Dent J*. 2008; 53(2): 128-32. DOI: <https://doi.org/10.1111/j.1834-7819.2008.00021.x>
75. Mickenautsch S, Yengopal V. Caries-preventive effect of high-viscosity glass ionomer and resin-based fissure sealants on permanent teeth: a systematic review of clinical trials. *PLoS One* 2016; 11(1): e0146512. DOI: <https://doi.org/10.1371/journal.pone.0146512>
76. Raggio DP, Tedesco TK, Calvo AF, Braga MM. Do glass ionomer cements prevent caries lesions in margins of restorations in primary teeth?: a systematic review and meta-analysis. *J Am Dent Assoc*. 2016; 147(3): 177-85. DOI: <https://doi.org/10.1016/j.adaj.2015.09.016>
77. Al Zraikat H, Palamara JE, Messer HH, Burrow MF, Reynolds EC. The incorporation of casein phosphopeptide-amorphous calcium phosphate into a glass ionomer cement. *Dent Mater*. 2011; 27(3): 235-43. DOI: <https://doi.org/10.1016/j.dental.2010.10.008>
78. Mazzaoui SA, Burrow MF, Tyas MJ, Dashper SG, Eakins D, Reynolds EC. Incorporation of casein phosphopeptide-amorphous calcium phosphate into a glass-ionomer cement. *J Dent Res*. 2003; 82(11): 914-8. DOI: <https://doi.org/10.1177/154405910308201113>

79. Wong RH, Palamara JE, Wilson PR, Reynolds EC, Burrow MF. Effect of CPP-ACP addition on physical properties of zinc oxide non-eugenol temporary cements. *Dent Mater.* 2011; 27(4): 329–38. DOI: <https://doi.org/10.1016/j.dental.2010.11.011>
80. Bahari M, Savadi Oskoe S, Kimyai S, Pouralibaba F, Farhadi F, Norouzi M. Effect of casein phosphopeptide-amorphous calcium phosphate treatment on microtensile bond strength to carious affected dentin using two adhesive strategies. *J Dent Res Dent Clin Dent Prospects.* 2014; 8(3): 141-7. DOI: <https://doi.org/10.5681/joddd.2014.026>
81. Al-Kawari HM, Al-Jobair AM. Effect of different preventive agents on bracket shear bond strength: in vitro study. *BMC Oral Health.* 2014; 14: 28
82. Ladhe KA, Sastri MR, Madaan JB, Vakil KK. Effect of remineralizing agents on bond strength of orthodontic brackets: an in vitro study. *Prog Orthod.* 2014; 15(1): 28. DOI: <https://doi.org/10.1186/s40510-014-0028-y>
83. Park SY, Cha JY, Kim KN, Hwang CJ. The effect of casein phosphopeptide amorphous calcium phosphate on the in vitro shear bond strength of orthodontic brackets. *Korean J Orthod.* 2013; 43(1): 23-8. DOI: <https://doi.org/10.4041/kjod.2013.43.1.23>
84. Yang H, Pei D, Chen Z, Lei J, Zhou L, Huang C. Effects of the application sequence of calcium-containing desensitising pastes during etch-and-rinse adhesive restoration. *J Dent.* 2014; 42(9): 1115-23. DOI: <https://doi.org/10.1016/j.jdent.2014.03.018>
85. Shadman N, Ebrahimi SF, Shoul MA, Sattari H. In vitro evaluation of casein phosphopeptide-amorphous calcium phosphate effect on the shear bond strength of dental adhesives to enamel. *Dent Res J (Isfahan).* 2015; 12(2): 167-72
86. Borges BC, Souza-Junior EJ, da Costa Gde F, Pinheiro IV, Sinhoreti MA, Braz R et al. Effect of dentin pre-treatment with a casein phosphopeptide-amorphous calcium phosphate (CPP-ACP) paste on dentin bond strength in tridimensional cavities. *Acta Odontol Scand.* 2013; 71(1): 271-7. DOI: <https://doi.org/10.3109/00016357.2012.671364>
87. Borges BC, Catelan A, Sasaki RT, Ambrosano GM, Reis AF, Aguiar FH. Effect of the application of a casein phosphopeptide-amorphous calcium phosphate (CPP-ACP) paste and adhesive systems on bond durability of a fissure sealant. *Odontology.* 2013; 101(1): 52-9. DOI: <https://doi.org/10.1007/s10266-012-0062-5>
88. Sattabanasuk V, Burrow MF, Shimada Y, Tagami J. Bonding of resin luting cements to dentine after casein phosphopeptide-amorphous calcium phosphate (CPP-ACP) treatment. *Int J Adhes Adhes.* 2014; 54: 93-9. DOI: <https://doi.org/10.1016/j.ijadhadh.2014.05.008>